



**HAL**  
open science

# Co-delivery of PLGA nanoparticles loaded with rSAG1 antigen and TLR ligands: An efficient vaccine against chronic toxoplasmosis

Mojgan Allahyari, Majid Golkar, Pezhman Fard-Esfahani, Isabelle Dimier-Poisson, Marie-Nöelle Ménélec

► **To cite this version:**

Mojgan Allahyari, Majid Golkar, Pezhman Fard-Esfahani, Isabelle Dimier-Poisson, Marie-Nöelle Ménélec. Co-delivery of PLGA nanoparticles loaded with rSAG1 antigen and TLR ligands: An efficient vaccine against chronic toxoplasmosis. *Microbial Pathogenesis*, 2022, 162, 11 p. 10.1016/j.micpath.2021.105312 . hal-03470174

**HAL Id: hal-03470174**

**<https://hal.inrae.fr/hal-03470174v1>**

Submitted on 5 Jan 2024

**HAL** is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

Copyright

1     **Co-delivery of PLGA nanoparticles loaded with rSAG1 antigen and TLR ligands : an**  
2                             **efficient vaccine against chronic toxoplasmosis**

3  
4     Mojgan Allahyari<sup>a</sup>, Majid Golkar<sup>b</sup>, Pezhman Fard-Esfahani<sup>c</sup>, Isabelle Dimier-Poisson<sup>d</sup>, Marie-  
5     Noëlle Mévélec<sup>d\*</sup>

6  
7     <sup>a</sup> Recombinant Protein Production Department, Research and Production Complex, Pasteur  
8     Institute of Iran, Karaj, Iran

9     <sup>b</sup> Molecular Parasitology Laboratory, Department of Parasitology, Pasteur Institute of Iran,  
10    Tehran, Iran

11    <sup>c</sup> Department of Biochemistry, Pasteur Institute of Iran, Tehran, Iran

12    <sup>d</sup> Université de Tours, INRAE, ISP, F-37000, Tours, France

13    \*Corresponding Author

14  
15    **Mojgan Allahyari** (*Recombinant Protein Production Department, Research and Production*  
16    *Complex, Pasteur Institute of Iran, Karaj, Iran.*), mojalah@yahoo.com

17    **Majid Golkar** (*Molecular Parasitology Laboratory, Department of Parasitology, Pasteur*  
18    *Institute of Iran, Tehran, Iran.*), Golkar@pasteur.ac.ir

19    **Pezhman Fard-Esfahani** (*Department of Biochemistry, Pasteur Institute of Iran, Tehran,*  
20    *Iran.*), Fard-esfahani@pasteur.ac.ir

21    **Isabelle Dimier-Poisson** (*Université de Tours, INRAE, ISP, F-37000, Tours, France*),  
22    dimier@univ-tours.fr

23    **Marie-Noëlle Mévélec** (*Université de Tours, INRAE, ISP, F-37000, Tours, France*),  
24    mevelec@univ-tours.fr

25  
26    **Abstract**

27    Although vaccination is a promising approach for the control of toxoplasmosis, there is  
28    currently no commercially available human vaccine. Adjuvants such as delivery vehicles and  
29    immunomodulators are critical components of vaccine formulations. In this study, Poly (D, L-  
30    lactide-co-glycolide) (PLGA) nanoparticles were applied to serve as delivery system for both  
31    surface antigen-1 (SAG1), a candidate vaccine against toxoplasmosis and two TLR ligands,  
32    monophosphoryl lipid A (MPL) and imiquimod (IMQ), respectively.

33    Compared to rSAG1 alone, CBA/J mice immunized with rSAG1-PLGA produced higher  
34    anti-SAG1 IgG antibodies titers. This response was increased by the co-administration of

35 IMQ-PLGA ( $p < 0.01$ ). Compared to IMQ-PLGA co-administration, MPL-PLGA co-  
36 administration further increased the humoral response ( $p < 0.01$ ) and potentiated the Th1  
37 humoral response. Compared to rSAG1 alone, rSAG1-PLGA, or rSAG1-PLGA mixed with  
38 IMQ-PLGA or MPL-PLGA similarly enhanced the cellular response characterized by the  
39 production of IFN- $\gamma$ , IL-2, TNF- $\alpha$  and low levels of IL-5, indicating a Th1-biased immunity.  
40 The induced immune responses, led to significant brain cyst reductions ( $p < 0.01$ ) after oral  
41 challenge with *T. gondii* cysts in mice immunized with either rSAG1-PLGA, rSAG1-PLGA +  
42 IMQ-PLGA, rSAG1-PLGA + MPL-PLGA formulations.  
43 Taken together the results indicated that PLGA nanoparticles could serve as a platform for  
44 dual-delivery of antigens and immunomodulators to provide efficacious vaccines against  
45 toxoplasmosis.

46

#### 47 **Keywords**

48 *Toxoplasma gondii*, rSAG1, Poly (D, L-lactide-co-glycolide) PLGA, Monophosphoryl lipid  
49 A, Imiquimod.

50

#### 51 **1. Introduction**

52 *Toxoplasma gondii* is an obligatory intracellular protozoan parasite with a considerably  
53 worldwide distribution which estimates to infect more than one-third of human population.  
54 Although immunocompetent individuals are rarely affected by toxoplasmosis, it still remains  
55 as major health concern and makes serious consequences in immunocompromised patients  
56 caused by AIDS or chemotherapy and in developing fetus due to mother's primary infection  
57 [1]. Undoubtedly, vaccination is known as the most promising approach against  
58 toxoplasmosis. Firstly, primary infection confers protective immunity against re-infection  
59 confirming the potential of vaccination [2]. On the other hand, available therapeutics do not  
60 eradicate tissue cysts and share severe side effects [3]. Protective immune response to *T.*  
61 *gondii* and other intracellular parasites is complicated and involves the collaboration of innate  
62 immunity, humoral and cellular acquired immunity, directed against the multi stages of the  
63 parasite [4]. Appropriate adaptive immune response depends mainly on the ability of CD4<sup>+</sup>  
64 and CD8<sup>+</sup> T lymphocytes to produce IFN- $\gamma$  [5]. Along with immune T cells, antibodies  
65 contribute also to protection [6]. Therefore, if vaccination enhances potent Th1 T cell  
66 responses, it can successfully provide protective immunity to *Toxoplasma* infection.

67 Among numerous *T. gondii* antigens, surface antigen 1 (SAG1) has attracted many  
68 attentions in vaccine development due to remarkable characteristics [7]. Subunit vaccine

69 candidates based on native or recombinant SAG1 proteins have been evaluated in animal  
70 models against, acute, chronic and congenital toxoplasmosis, using various adjuvant  
71 formulations to overcome the low intrinsic immunogenicity of the protein [8]. Immune  
72 responses and significant protections were obtained in most of these studies.

73 With the continuous improvement of knowledge and awareness regarding the immune  
74 system, the application of vaccine delivery strategies such as Poly (D, L-lactic-co-glycolic  
75 acid) (PLGA) particles could bring hope to improve vaccine efficacy [9]. Indeed, we  
76 previously showed that rSAG1 adsorbed on the surface of PLGA nanoparticles or rSAG1  
77 encapsulated in PLGA nanoparticles elicited higher systemic IFN- $\gamma$  and specific anti-*T. gondii*  
78 IgG antibodies than rSAG1 alone and conferred significant protection against acute  
79 toxoplasmosis [10]. Similar results were also obtained with rSAG1 protein [11] and a  
80 multimeric recombinant *T. gondii* vaccine including SAG1 epitopes [12] or a recombinant  
81 chimeric protein rSAG1/2 [13] combined with PLGA nano-or microparticles.

82 TLRs agonists belong to a class of adjuvant known as immune stimulating agents. TLRs  
83 not only mediate the activation of innate immune cells, but also directly modulate vaccine  
84 specific response [14]. MPL, a portion of *Salmonella minnesota* lipopolysaccharide  
85 peptidoglycan, as specific agonist of TLR4 has been applied in some vaccination studies  
86 against *T. gondii* infection. Golkar et al. [15] demonstrated the protective efficacy of  
87 recombinant GRA2 with MPL against chronic infection by *T. gondii* and confirmed the role  
88 of MPL as an efficient immunostimulator to induce a protective Th1 immune response. The  
89 MPL adjuvant with toxofilin DNA vaccine also induced significantly enhanced humoral and  
90 Th1-biased immune responses compared to the non-adjuvant toxofilin DNA vaccine [16].  
91 IMQ, a synthetic analog of imidazoquinoline family, as an agonist of TLR7 has been  
92 approved by US Food and Drug Administration (FDA) as an immunopotentiator agent for  
93 local topical administration [17]. Recently, IMQ has been considered as a candidate for use  
94 against *Toxoplasmosis* both therapeutically and prophylactically [18, 19], but there is not any  
95 research on vaccine design against *T. gondii*. Although TLR agonists are powerful immune  
96 stimulators, induced unwanted cytokine release syndrome leading to potential adverse events  
97 and safety concerns is a major factor limiting their usage. To minimize these side effects and  
98 to enhance their efficacy, TLR agonists are increasingly combined with delivery systems  
99 including PLGA particles [20-22].

100 As PLGA nanoparticles can serve for dual-delivery of antigens and immunomodulators, in  
101 present study, mice vaccination was performed with rSAG1-PLGA nanoparticles in  
102 combination with IMQ or MPL encapsulated into PLGA nanoparticles in order to assess their

103 impacts on eliciting immune responses and protection against *T. gondii* infection. Since, we  
104 previously proved that adsorption is a more suitable approach than encapsulation in antigen  
105 loading on PLGA nanoparticles [10], rSAG1-PLGA was prepared by adsorption method. It is  
106 worthy to note that during encapsulation process, protein exposure to water-oil interface,  
107 harsh mechanical, thermal and chemical stresses could affect protein integrity and  
108 consequently its immunogenicity [23]. Protection was evaluated against chronic infection in  
109 CBA/J mice susceptible to cyst formation and development of toxoplasmosis encephalitis. In  
110 addition, mice were challenged by the oral route, the major natural route of infection, with  
111 tissue cysts.

112  
113

## 114 **2. Materials and Method**

115

### 116 **2.1 Materials**

117

118 Poly (D, L-lactide-co-glycolide) polymer (PLGA), Resomer®RG503 (50:50, lactide:  
119 glycolide ratio) (viscosity 0.32-0.44 dl/g) was purchased from Boehringer Ingelheim,  
120 Germany. PVA [poly vinyl alcohol; molecular weight (MW) 30,000–70,000 Da, 88%  
121 hydrolyzed] was obtained from Sigma Chemical Company. The materials applied for SDS  
122 PAGE gel electrophoresis and protein molecular weight marker were supplied from Roche  
123 Applied Sciences (Mannheim, Germany) and Fermentas, Vilnius, Lithuania, respectively.  
124 Dichloromethane (DCM) (analytical grade) was obtained from Merck Ltd. Cell culture  
125 reagents including RPMI-1640, Fetal Calf Sera (FCS), HEPES, L-glutamine, sodium  
126 pyruvate, penicillin, and streptomycin, were obtained from Gibco (Life Technologies GmbH,  
127 Karlsruhe, Germany). Concanavalin A (conA), lyophilized powder of MPL (monophosphoryl  
128 from *Salmonella enterica* serotype *minnesota* Re 595) were purchased from Sigma-Aldrich  
129 (Darmstadt, Germany). Imiquimod Vacchi Grade™ was supplied from InvivoGen (CA, USA).  
130 All other chemicals used were of analytical reagent grade. All solutions were prepared by  
131 MilliQ™ ultrapure (Milli-QSystem, Millipore, Molsheim, France).

132

### 133 **2.2 Purification and characterization of rSAG1 protein**

134

135 rSAG1 protein was cloned, expressed and purified according to our previous studies and its  
136 purity, antigenicity, and immunogenicity were confirmed [24]. In order to remove of

137 contaminants including LPS, and *E.coli* DNA, Sartobind® Q strong 0.08 mL (Sartorius) was  
138 used. Briefly, rSAG1 buffer was exchanged to binding buffer of Sartobind® Q strong (Tris-  
139 HCl 20 mM, NaCl 50 mM, pH 8) by MicroSpin G-25 column. After column equilibration by  
140 mentioned buffer, rSAG1 was applied to Sartobind® Q strong. The Sartobind® Q strong  
141 operated as negative chromatography, so DNA attached to the column, and rSAG1 passed  
142 through Sartobind® Q strong. The concentration of bacterial endotoxin in purified rSAG1  
143 was measured by limulus amoebocyte lysate assay using LAL chromogenic endotoxin  
144 quantitation kit (Pierce®, Thermo scientific, USA).

145

### 146 ***2.3 The preparation of different nanoparticles***

147

148 Encapsulation of IMQ and MPL was carried out completely according to the preparation of  
149 blank PLGA mentioned in our previous study [10] using double emulsion solvent evaporation  
150 technique. The only distinction was the substitution of IMQ or MPL ligands for PBS. The  
151 IMQ and MPL were used in concentration of 5 mg/mL and 2.5 mg/mL, respectively. rSAG1  
152 was adsorbed on blank PLGA as stated by Allahyari et al. [25].

153 Various batches of individual PLGA nanoparticles loaded by IMQ, MPL, and rSAG1 were  
154 prepared to provide sufficient quantity of homogenous nanoparticles. rSAG1-PLGA  
155 nanoparticles were mixed with either IMQ-PLGA or MPL-PLGA nanoparticles to make  
156 different formulations **just** before each immunization.

157

### 158 ***2.4 Nanoparticles characterization***

159

#### 160 ***2.4.1 Particle size, zeta potential and polydispersity index***

161 The particle size (Z-average mean), particle size distribution (PSD), polydispersity index  
162 (PDI) and surface charge of all nanoparticles were determined based on Allahyari et al. [25].  
163 Both types of measurements were performed at 25°C using a ZetasizerNano ZS (Malvern  
164 Instruments, Worcestershire, UK). All measurements were performed in triplicate.

165

#### 166 ***2.4.2 Process yield determination***

167 Process yield for both blank PLGA nanoparticles and PLGA nanoparticles loaded by  
168 rSAG1, IMQ, and MPL were assessed in three preparation batches as mentioned in Allahyari  
169 et al. [10].

170

### 171 2.4.3 Evaluation of encapsulation efficiency

172 Encapsulation efficiency of IMQ, and MPL into PLGA nanoparticles was determined by  
173 direct methods. Therefore, after hydrolysis of individual encapsulated PLGA nanoparticles,  
174 the quantity of encapsulated IMQ and MPL was calculated in definite amount of PLGA  
175 nanoparticles. The quantification of IMQ was done using spectrophotometry. Standard  
176 calibration curve of IMQ was drawn by ascertaining adsorption of definite concentration of  
177 IMQ at 320 nm. Afterwards, IMQ encapsulated in PLGA nanoparticles was quantified against  
178 standard curve. The amount of encapsulated MPL into PLGA nanoparticles was calculated by  
179 reverse phase (RP) HPLC (Kenuver, AZURA) through the area under curve (AUC), in  
180 comparison with defined amount of MPL. Encapsulated MPL was extracted by methanol,  
181 chloroform solvents (2:1 v/v). After centrifugation (at 20000 rpm, 20 mins), 50  $\mu$ l of  
182 supernatant was loaded on TSKgel Octadecyl-4PW column (2.0 mm ID  $\times$  15.0 cm length,  
183 particle size 7.0  $\mu$ m) (TOSOH Bioscience). The elution was carried out with a linear gradient  
184 at a flow rate of 0.5 mL/min (Sykam delivery system S2100 and at 210 nm using UV detector  
185 (Sykam UV/Vis detector S3210) according to Kazzaz et al. [26]. Evaluation of all  
186 encapsulation efficiencies was evaluated by direct method according to following equation in  
187 triplicate:

188 Encapsulation efficiencies % = "Amount of TLR ligand encapsulated into PLGA  
189 nanoparticles"/"Total amount of TLR ligand used for encapsulation"  $\times$  100. Blank PLGA  
190 nanoparticles were used as negative control. The amount of rSAG1 adsorbed on PLGA  
191 nanoparticles was calculated as described by Allahyari et al. [25].

192

## 193 2.5 Vaccination studies

194

### 195 2.5.1 Mice immunization and Vaccination schedules

196 The 6-week-old female CBA/J (H-2k) mice (Janvier, Le Genest St. Isle, France) resistant  
197 to acute toxoplasmosis infection and susceptible to cyst formation in chronic infection were  
198 applied in present study. Mice were kept under pathogen-free conditions in the animal house  
199 of University of Tours. Experiments were performed in accordance with the guideline for  
200 animal experimentation (EU Directive 2010/63/EU) and the protocol was approved by the  
201 local ethics committee (number 00807-02, Comité d'Ethique en Expérimentation Animale  
202 Val de Loire). *In-vivo* studies were divided in two experiments. Vaccination groups in first  
203 experiment and second experiment were shown in table 1 and table 2, respectively. CBA/J  
204 (H-2k) mice were randomly divided into groups of 12 mice, except for IMQ-PLGA control

205 group in second experiment: only four mice for cellular analysis. All groups were immunized  
206 subcutaneously (s.c.) two times at 3-week intervals with different formulations containing 20  
207  $\mu\text{g}$  rSAG1, IMQ (64.5 $\mu\text{g}$ ), and MPL (34  $\mu\text{g}$ ), as represented in Table 1 and 2, respectively.

208

#### 209 2.5.2 *T. gondii* extract (TE) preparation

210 Preparation of TE containing both cytoplasmic and membrane antigens was prepared from  
211 tachyzoites of the RH strain obtained by serial passaging in human foreskin fibroblast (HFF)  
212 cell monolayers, as previously described [27]. Briefly, the obtained tachyzoites were washed  
213 in PBS and sonicated for three 10-min periods at 60 W/s. The *Toxoplasma* sonicate was  
214 centrifuged at 2,000 g for 30 min. The protein concentration was determined in the  
215 supernatant by the Micro BCA protein assay reagent kit using bovine serum albumin (BSA)  
216 as the standard (Pierce, Rockford, III.). The TE was stored at -20°C until use.

217

#### 218 2.5.3 Humoral response

219 Anti SAG1-specific IgG antibodies were measured by ELISA on sera collected three weeks  
220 after second immunization as previously described [27]. Briefly, Flat-bottomed 96-well plates  
221 (Nunc) were coated with 10  $\mu\text{g}/\text{mL}$  TE. Serial two-fold dilutions of serum were performed  
222 (starting at a 1:100 dilution) and added to the wells. Sample of naive mice (untreated) served  
223 as negative controls. Bound antibodies were detected with Goat anti-Mouse IgG alkaline  
224 phosphatase (1:5,000, Sigma). The optical density of each sample was read at 405 nm. The  
225 endpoint antibody titer for each sample is given as the reciprocal of the highest dilution  
226 producing an OD that was 2.5-fold greater than that of the serum of naïve mice (serum of  
227 naïve mice gave optical density readings of less 0.1).

228 The levels of anti-SAG1 IgG subclasses were measured by ELISA as described above, except  
229 that sera were added to the plates at a single dilution (1:100 for sera of mice immunized with  
230 rSAG1, rSAG1-PLGA, rSAG1-PLGA and IMQ-PLGA, PLGA, IMQ-PLGA or MPL-PLGA  
231 nanoparticles and 1:800 for sera of mice immunized with rSAG1-PLGA and MPL-PLGA  
232 nanoparticles). The alkaline phosphatase-conjugated Rat anti-Mouse IgG1 and IgG2a were  
233 used at 1:1,000 (BD Pharmingen). IgG subclasses were evaluated using optical density.

234

#### 235 2.5.4 Western Blotting

236 Western blottings were performed as previously described with either rSAG1 or *T. gondii*  
237 extract as the source of antigen and pooled sera obtained from mice in each group three weeks  
238 after second immunizations [27]. rSAG1 (6  $\mu\text{g}/1\text{-cm-wide slot}$ ) or TE (60  $\mu\text{g}/1\text{-cm-wide slot}$ )



239 were electrophoresed in a 12 % SDS–polyacrylamide gel (SDS-PAGE) under non-reducing  
240 conditions, transferred to nitrocellulose, and probed with pooled sera from untreated mice (T-  
241 ), *T. gondii* infected mice (inf), mice immunized with soluble rSAG1 in PBS (G1), rSAG1-  
242 PLGA (G2), rSAG1-PLGA and IMQ-PLGA (G3), PLGA (G4) or IMQ-PLGA (G5). Sera  
243 were diluted at 1:100. A mouse monoclonal antibody (mAb), anti-SAG1 MAb 1E5 (diluted  
244 at 1:100) is used as positive control [28]. **Anti-SAG1 mAb 1E5 was kindly provided by Jean-**  
245 **François Dubremetz.**

246

#### 247 *2.5.5 Cellular response (cytokine assay)*

248 Four mice in each group were sacrificed three weeks after the last immunization. Single  
249 spleen cell suspensions were individually obtained by filtration through nylon mesh.  
250 Erythrocytes were removed by lysis (hypotonic shock) and the remaining cells were washed  
251 and suspended in RPMI 1640 medium supplemented with 5% FBS, 25 mM HEPES, 2 mM L-  
252 glutamine, 1 mM sodium pyruvate, 50  $\mu$ M  $\beta$ -mercaptoethanol, 100 U/mL penicillin, and 100  
253  $\mu$ g/mL streptomycin. Cells ( $5 \times 10^5$  cells/well) were stimulated in triplicate with 4  $\mu$ g/mL  
254 **endotoxin depleted** rSAG1, or with medium alone (negative control). Concanavalin A (5  
255  $\mu$ g/mL) was used as a positive control for proliferation. Supernatants were harvested and  
256 assayed for IL-2 after 24 h and for IFN- $\gamma$ , IL-5, IL-10 after 72 h. The concentrations of  
257 cytokines were determined using ELISA kits (eBioscience, San Diego, CA) according to the  
258 manufacturer's protocol. Cytokine concentrations were determined by reference to standard  
259 curves constructed with known amounts of cytokines provided by the kits.

260

#### 261 *2.5.6 Challenge*

262 Mice (8/group) were orally challenged with 15 cysts of the 76K *T. gondii* strain, three  
263 weeks after the last immunization. To evaluate the protection, brain cyst loads were evaluated  
264 one month after challenge. Mouse brains were homogenized in 5 mL of RPMI medium, and  
265 the number of tissue cysts per brain was determined microscopically by counting 8 samples  
266 (10  $\mu$ l) of each mouse brain by light microscope.

267

#### 268 *2.6 Statistical analyses*

269

270 Statistical significance was analyzed using GraphPad Prism software. Statistical analysis  
271 was done by one-way ANOVA followed by a Tukey's multiple comparison test or using a

272 Kruskal–Wallis test followed by Dunn’s multiple comparison test.  $p < 0.05$  was considered  
273 to be statistically significant.

274

### 275 **3. Results**

276

#### 277 ***3.1 Production of rSAG1***

278

279 rSAG1 was expressed and purified, its antigenicity and immunogenicity were confirmed as  
280 described in our previous study [24]. Endotoxin concentration in purified protein was  
281 determined less than 0.05 EU/ $\mu$ g by limulus amoebocyte lysate assay.

282

#### 283 ***3.2 Nanoparticles characterization***

284

285 All different nanoparticles were identified regarding zeta average size, PDI, zeta potential,  
286 encapsulation efficiency and process yield. The results were summarized in Table 3.

287 The sizes of IMQ-PLGA and MPL-PLGA were about  $451.3 \pm 27$  and  $403 \pm 25$  nm,  
288 respectively. There was significant difference ( $p < 0.05$ ) between mean sizes of MPL-PLGA  
289 and IMQ-PLGA or rSAG1-PLGA nanoparticles. The difference between mean sizes of IMQ-  
290 PLGA and rSAG1-PLGA was not significant. All prepared nanoparticles share a PDI less  
291 than 0.2.

292 Surface charges of IMQ-PLGA, MPL-PLGA, nanoparticles were negative,  $-4.9 \pm 0.26$  and -  
293  $5.6 \pm 0.75$  mV, respectively. Among all nanoparticles, rSAG1-PLGA showed the lowest  
294 negative charge about  $-2.37 \pm 0.3$  mV. Zeta potential in rSAG1-PLGA was significantly ( $p <$   
295  $0.001$ ) lower than all other PLGA nanoparticles.

296 All statistical analysis was done by one way ANOVA. The efficacy of IMQ encapsulation  
297 into IMQ-PLGA nanoparticles measured by spectrophotometry method was about  $70 \pm 3.1$  %  
298 (Table 3), which was calculated through interpolating of absorbance with the concentration.  
299 In addition, as shown in Table 3, the encapsulation efficacy of MPL into MPL-PLGA  
300 nanoparticles was quantified by RP-HPLC through comparison of AUC of encapsulated MPL  
301 and AUC related to defined amount of MPL, nearly  $73.1 \pm 1.2$  (Fig.1).

302 The adsorption efficacy of rSAG1-PLGA nanoparticles was  $69.01 \pm 1.8$  %. Blank PLGA  
303 and rSAG1-adsorbed PLGA were prepared as mentioned by Allahyari et al. [25]. The results  
304 represent mean  $\pm$  SD of 5 independent PLGA nanoparticle preparations.

305

306 Fig. 1. **Quantification of encapsulated MPL in MPL-PLGA nanoparticles by RP-HPLC**  
307 **(Knauer, AZURA)**. The numbers presented on graphs demonstrated area under curve  
308 (AUC). Std, standard, is referred to defined amount of MPL. The column specification;  
309 TSKgel Octadecyl-4PW column (2.0 mm ID × 15.0 cm length, particle size 7.0 μm) (TOSOH  
310 Bioscience).

311

### 312 **3.3 Vaccination with rSAG1-PLGA in combination with IMQ-PLGA**

313

314 The effect of IMQ adjuvant, when encapsulated into PLGA and co-administrated with  
315 rSAG1-PLGA was first investigated. CBA/J mice (12 mice/group) were immunized  
316 subcutaneously (s.c.) two times at 3 weeks interval with rSAG1-PLGA nanoparticles or with  
317 the mixture of rSAG1-PLGA and IMQ-PLGA nanoparticles. Control mice were immunized  
318 with rSAG1 in PBS, blank PLGA nanoparticles or IMQ-PLGA nanoparticles (Table 1). The  
319 induced humoral and cellular immune responses and the protective efficacy against chronic  
320 toxoplasmosis following oral challenge, were evaluated.

321

#### 322 **3.3.1 Humoral immune responses**

323 The humoral response was analyzed three weeks after the second immunization.  
324 Immunoblot analysis of mouse sera was first performed against rSAG1 (Fig. 2A). Sera from  
325 mice immunized either with rSAG1, rSAG1-PLGA or rSAG1-PLGA and IMQ-PLGA reacted  
326 mainly with two protein bands corresponding to rSAG1 monomers at the expected size  
327 (around 30 kDa). These sera reacted also with dimers (around 70 kDa) and probably  
328 multimers of rSAG1 (> 70 kDa). These bands are also recognized by serum IgG antibodies  
329 from *T. gondii* infected mice (inf). Monoclonal antibody 1E5 reacted only with the two  
330 protein bands corresponding to rSAG1 monomers. Monoclonal antibody 1E5 recognizes a  
331 conformational epitope which may not be accessible (or problem of conformation) in the  
332 multimeric forms of rSAG1. Importantly, immunoblot analysis of mouse sera performed  
333 against *T. gondii* extract, showed that sera from mice immunized either with rSAG1, rSAG1-  
334 PLGA or rSAG1-PLGA and IMQ-PLGA reacted strongly with native SAG1 (Fig. 2B). As  
335 expected, sera from mice immunized with PLGA (G4) and IMQ-PLGA (G5), and untreated  
336 mice (T-) identified no protein in rSAG1 or *T. gondii* extract.

337 ELISA using *T. gondii* extract containing native SAG1 as coating antigen was used to  
338 determine endpoint anti-SAG1 IgG antibodies titers (Fig. 2C). In our experimental conditions,  
339 anti-SAG1-specific IgG antibodies were detected only in 6/12 mice immunized with rSAG1

340 in PBS (for 6 mice, OD value failed to reach 2.5 times the background value at the initial  
341 dilution tested), whereas all mice immunized with rSAG1-PLGA nanoparticles produced  
342 detectable anti-SAG1-specific IgG antibodies. These results indicated that a stronger humoral  
343 immune response was induced in mice immunized with rSAG1-PLGA nanoparticles  
344 compared to mice immunized with rSAG1 alone, however, the difference between the two  
345 immunized groups did not reach statistical significance. In mice immunized with rSAG1-  
346 PLGA and IMQ-PLGA nanoparticles, higher antibodies titers were found compared to mice  
347 immunized either with rSAG1 in PBS or rSAG1-PLGA nanoparticles, however, a significant  
348 statistical difference was found only between the rSAG1 and rSAG1-PLGA+IMQ-PLGA  
349 groups ( $p < 0.01$ ). Mice vaccinated with PLGA nanoparticles or IMQ-PLGA nanoparticles  
350 did not produce any anti-SAG1 antibodies. To find out whether a Th1 and/or a Th2 humoral  
351 response was induced by immunization, the IgG subclasses were analyzed (Fig 2D). The  
352 levels of IgG1 exceeded those of IgG2a in sera of mice immunized with PLGA nanoparticles  
353 with or without IMQ (IgG1/IgG2a OD ratio  $> 2$ ), suggesting mixed Th1/Th2 humoral-type  
354 response with a bias towards a Th2 response. In conclusion, vaccination with the mixture of  
355 rSAG1-PLGA and IMQ-PLGA enhanced a mixed Th1/Th2 humoral response with a bias  
356 towards a Th2 response.

357

358 **Fig. 2. Specific antibody response in mice immunized with rSAG1-PLGA nanoparticles**  
359 **or the mixture of rSAG1-PLGA and IMQ-PLGA nanoparticles.** Analysis of humoral  
360 response was done three weeks after second immunization. For immunoblot analysis, rSAG1  
361 (A) or *T. gondii* extract (B) electrophoresed and transferred to nitrocellulose, were probed  
362 with pooled sera from immunized mice, *T. gondii* infected mice (inf) and untreated mice (T-).  
363 A mouse mAb (anti-SAG1 MAb 1E5) was used as positive control (mAb). The molecular  
364 weights are shown on the left side. Sera and mAb 1E5 were diluted at 1:100. mAb (anti-  
365 SAG1 MAb 1E5), inf (*T. gondii* infected mice), G1 (rSAG1), G2 (rSAG1-PLGA), G3  
366 (rSAG1-PLGA + IMQ-PLGA), G4 (PLGA), and G5 (IMQ-PLGA), T- (untreated mice).  
367 C) Determination of specific anti-SAG1 antibody titers by ELISA using *T. gondii* extract as  
368 coating antigen. Sera from each mouse in each group ( $n = 12/\text{group}$ ) were analyzed  
369 individually. The antigen-specific antibody titer (endpoint titer) was given as the reciprocal of  
370 the highest dilution making an optical density (OD) that was 2.5-fold greater than that of the  
371 serum of non-immunized mice. Dotted line represent the lowest mouse sera dilution tested.  
372 Titers below the limit of detection ( $< 100$ ) were assigned a value of 50 for analysis. Symbols

373 represent individual animals. Results are presented on scatter plots as geometric mean with  
374 the 95% confidence interval. Kruskal-Wallis, Dunn's multiple comparisons test.  $**p < 0.01$   
375 **D)** Determination of the IgG subclasses profiles by ELISA using *T. gondii* extractas coating  
376 antigen. Sera were collected from six mice in each group and evaluated individually. Results  
377 are expressed as the mean of the optical density (OD)  $\pm$  SEM. Sera were tested at a single  
378 dilution (1 :100).

379

### 380 3.3.2 Cellular immune responses

381 The potency of the various formulations to induce T cell immune responses was  
382 investigated by measuring the specific cytokine responses in spleen three weeks after second  
383 immunization. Splenocytes from mice immunized with rSAG1-PLGA or the mixture of  
384 rSAG1-PLGA and IMQ-PLGA nanoparticles elicited significant ( $p < 0.05$ ) amounts of IFN- $\gamma$ ,  
385 IL-2, TNF- $\alpha$  (Th1 cytokines) and IL-5 (Th2 cytokine) in response to rSAG1 stimulation  
386 compared to their respective control (PLGA and IMQ-PLGA, respectively). However, any  
387 significant difference in cytokine production was shown between the two above-mentioned  
388 immunized groups. Furthermore, splenocytes from mice immunized with rSAG1 elicited very  
389 low levels of IFN- $\gamma$ , IL-2, TNF- $\alpha$  and IL-5 as compared to mice immunized with rSAG1-  
390 PLGA or the mixture of rSAG1-PLGA and IMQ-PLGA. In addition, the amounts of IFN- $\gamma$ ,  
391 TNF- $\alpha$ , IL-5 ( $p < 0.05$ ) in mice immunized with rSAG1-PLGA and the level of IL-2 ( $p <$   
392  $0.01$ ) in mice immunized with the mixture of rSAG1-PLGA and IMQ-PLGA were  
393 significantly higher than those in mice immunized by rSAG1. Although the level of IL-5  
394 significantly increased in groups immunized with rSAG1-PLGA and the mixture of rSAG1-  
395 PLGA and IMQ-PLGA nanoparticles in comparison with control groups, all immunized  
396 groups and control groups share a considerably low amount of induced IL-5.

397

398 **Fig. 3. Cellular immune response in mice immunized with rSAG1-PLGA nanoparticles**  
399 **or the mixture of rSAG1-PLGA and IMQ-PLGA nanoparticles.** Three weeks after the  
400 second immunization, splenocytes were collected from four mice in each group, and cultured  
401 with 4  $\mu$ g/mL rSAG1 or with medium alone (no stimulation). Cell-free supernatants were  
402 harvested after 24 (IL-2) or 72 h (IFN- $\gamma$ , IL-5, and TNF- $\alpha$ ) for cytokine assays. Results are  
403 expressed as the median and interquartile range. Kruskal-Wallis, Dunn's multiple  
404 comparisons test.  $*p < 0.05$ ;  $**p < 0.01$  significant differences between the immunized  
405 groups.

406

### 407 3.3.3 Challenge studies

408 In order to evaluate the protective effect of these vaccine formulations against chronic  
409 toxoplasmosis, mice were orally challenged with 15 cysts of the 76K strain 3 weeks after the  
410 second immunization and sacrificed one month after challenge.

411 The numbers of brain cyst after challenge were significantly decreased in mice immunized  
412 with the mixture of rSAG1-PLGA and IMQ-PLGA compared to both control groups ( $p < 0.05$   
413 compared to PLGA control group;  $p < 0.01$  compared to IMQ-PLGA control group,  
414 respectively). In addition, the reduction in brain cyst load was attained in rSAG1-PLGA  
415 immunized mice compared to IMQ-PLGA control group ( $p < 0.05$ ), but not compared to  
416 PLGA control group. Mice immunized with the mixture of rSAG1-PLGA and IMQ-PLGA  
417 and mice immunized with rSAG1-PLGA shared the least brain cyst loads about 51% and 42%  
418 brain cyst reduction, respectively, versus control IMQ-PLGA group ( $p < 0.01$ ). However, the  
419 difference between these two groups did not meet any statistical significance. Moreover, mice  
420 immunized with rSAG1 alone did not show any significant reduction in brain cyst compared  
421 to control groups.

422

423 **Fig. 4. Evaluation of the protection against chronic toxoplasmosis in mice immunized**  
424 **with rSAG1-PLGA nanoparticles or the mixture of rSAG1-PLGA and IMQ-PLGA**  
425 **nanoparticles.** Mice in all groups were orally challenged with 15 cysts of the 76 K strain 3  
426 weeks after the second immunization. One month after challenge, all mice were sacrificed ( $n$   
427 = 8/group) and the number of brain cysts in each mouse was calculated individually. Data  
428 represent the mean  $\pm$  SEM of measurements from eight mice. ANOVA, Tukey's multiple  
429 comparison test. \* $p < 0.05$  and \*\* $p < 0.01$ .

430

### 431 3.4 Vaccination with rSAG1-PLGA in combination with IMQ-PLGA or MPL-PLGA

432

433 After the investigation of the effect of IMQ, effect of MPL adjuvant, when encapsulated  
434 into PLGA and co-administrated with rSAG1-PLGA, was evaluated. CBA/J mice were  
435 immunized subcutaneously (s.c.) two times at 3 week intervals with the mixture of rSAG1-  
436 PLGA and MPL-PLGA nanoparticles (12 mice) or with the mixture of rSAG1-PLGA and  
437 IMQ-PLGA nanoparticles (12 mice). Control mice were immunized with MPL-PLGA (12  
438 mice) or IMQ-PLGA nanoparticles (4 mice) for the analysis of the cellular immune response  
439 (Table2).

440

### 441 3.4.1 Humoral immune responses

442 Higher endpoint anti- SAG1 IgG titers were found in mice immunized with rSAG1-PLGA  
443 and MPL-PLGA nanoparticles (Fig 5A), compared to mice immunized with rSAG1-PLGA  
444 and IMQ-PLGA nanoparticles ( $p < 0.01$ ). In both groups, the levels of IgG1 exceeded those  
445 of IgG2a (Fig 5B) with a IgG1/IgG2a OD ratio slightly different (rSAG1-PLGA and IMQ-  
446 PLGA nanoparticles, ratio  $> 2$ ; rSAG1-PLGA and MPL-PLGA nanoparticles, ratio  $< 2$ ).  
447 Compared to IMQ, MPL potentiated the humoral response and induced a more balanced  
448 Th1/Th2 humoral response (IgG1/IgG2a OD around 1.5).

449

### 450 **Fig. 5. Specific antibody response in mice immunized with the mixture of rSAG1-PLGA** 451 **and MPL-PLGA or with the mixture of rSAG1-PLGA and IMQ-PLGA nanoparticles.**

452 Analysis of humoral response was done three weeks after the second immunization. **A).**  
453 Determination of specific anti-SAG1 antibody titers by ELISA using *T. gondii* as coating  
454 antigen. Sera from each mouse in each group were analyzed individually ( $n = 12$ /group,  
455 except for IMQ-PLGA nanoparticles group,  $n = 4$ ). The antigen-specific antibody titer  
456 (endpoint titer) was given as the reciprocal of the highest dilution making an optical density  
457 (OD) that was 2.5-fold greater than that of the serum of non-immunized mice. Dotted line  
458 represent the lowest mouse sera dilution tested. Symbols represent individual animals. Results  
459 are presented on scatter plots as geometric mean with the 95% confidence interval. Kruskal-  
460 Wallis, Dunn's multiple comparisons test.  $**p < 0.01$ . **B)** Determination of the IgG subclasses  
461 profiles by ELISA using *T. gondii* extract as coating antigen. Sera ( $n = 6$ /group, except for  
462 IMQ-PLGA nanoparticles group  $n = 4$ ) were evaluated individually. Results are expressed as  
463 the mean of the optical density (OD)  $\pm$  SEM. Sera were tested at a single dilution (rSAG1-  
464 PLGA + IMQ-PLGA group and control groups, dilution 1:100 ; rSAG1-PLGA + IMQ-PLGA  
465 group, dilution 1:800 ).

466

467

### 468 3.4.2 Cellular immune responses

469 Splenocytes from mice immunized with the mixture of rSAG1-PLGA and IMQ-PLGA  
470 nanoparticles or rSAG1-PLGA and MPL-PLGA nanoparticles elicited significant ( $p < 0.05$ )  
471 levels of IFN- $\gamma$ , IL-2, TNF- $\alpha$  (Th1 cytokines) and IL-5 (Th2 cytokine) in response to rSAG1  
472 stimulation compared to their respective control (IMQ-PLGA and MPL-PLGA, respectively).

473 More IL-2 and IFN- $\gamma$  were found in the supernatants of restimulated splenocytes from mice  
474 immunized with the mixture of rSAG1-PLGA and MPL-PLGA nanoparticles compared to  
475 those from mice immunized with rSAG1-PLGA and IMQ-PLGA. However the differences  
476 did not reach statistical significance.

477

478 **Fig. 6. Cellular immune response in mice immunized with the mixture of rSAG1-PLGA**  
479 **and MPL-PLGA or with the mixture of rSAG1-PLGA and IMQ-PLGA nanoparticles.**

480 Three weeks after the second immunization, splenocytes were collected from four mice in  
481 each group, and cultured with 4  $\mu$ g/mL rSAG1 or medium alone (no stimulation). Cell-free  
482 supernatants were harvested after 24 (IL-2) or 72 h (IFN- $\gamma$ , IL-5, and TNF- $\alpha$ ) for cytokine  
483 assays. Results were expressed as the median and interquartile range. Mann Whitney test was  
484 done. "ns", no significant difference between the two immunized groups.

485

486

#### 487 *3.4.3 Challenge studies*

488 Significant protection was displayed in the group of mice immunized with the mixture of  
489 rSAG1-PLGA and MPL-PLGA compared to its control group (MPL-PLGA) ( $p < 0.01$ ),  
490 demonstrating 41% brain cyst reduction. The brain cyst number of mice immunized with the  
491 mixture of rSAG1-PLGA and MPL-PLGA was similar to that of mice immunized with the  
492 mixture of rSAG1-PLGA and IMQ-PLGA (1583  $\pm$  427 versus 1698  $\pm$  519). These results  
493 suggest that in our experimental conditions, MPL and IMQ have similar protective effects  
494 against chronic toxoplasmosis when encapsulated into PLGA nanoparticles and co-  
495 administrated with rSAG1-PLGA nanoparticles.

496

497 **Fig. 7. Evaluation of the protection against chronic toxoplasmosis in mice immunized**  
498 **with the mixture of rSAG1-PLGA and MPL-PLGA or with the mixture of rSAG1-**  
499 **PLGA and IMQ-PLGA nanoparticles.** Mice in all groups were orally challenged with 15

500 cysts of the 76 K strain, 3 weeks after second immunization. One month after challenge, all  
501 mice were sacrificed and the number of brain cysts in each mouse was calculated  
502 individually. Data represent the mean  $\pm$  SEM of measurements from eight mice. ANOVA,  
503 Tukey's multiple comparison test.  $**p < 0.01$ ; "ns", no significant difference.

504

505



#### 506 4. Discussion

507

508 The main goal of this study was to investigate the adjuvanticity of IMQ and MPL loaded  
509 into PLGA nanoparticles when administrated with rSAG1 antigen adsorbed on PLGA  
510 nanoparticles and to compare the protective efficacies against *T. gondii* chronic infection in  
511 CBA/J after challenge with *T. gondii* cysts by the oral route. It has been well established that  
512 vaccine delivery systems can compensate for poor immunogenicity of subunit vaccines.  
513 Hence, both PLGA micro and nanoparticles were applied to serve as delivery system and  
514 adjuvant dual role for recombinant SAG1 proteins [11, 29], a multimeric recombinant *T.*  
515 *gondii* vaccine including SAG1 epitopes [12] or a recombinant chimeric protein rSAG1/2  
516 [13]. To further potentiate protective immunity, particulate delivery of rSAG1 can be co-  
517 administrated with an immunostimulant molecule.

518 In our design, IMQ and MPL that target TLR7/8 and TLR4, respectively, were  
519 encapsulated in PLGA nanoparticles to be co-administrated with rSAG1 adsorbed on PLGA  
520 nanoparticles. Among the properties of PLGA nanoparticles including size, shape, surface  
521 charge and hydrophobicity, particle sizes are of high priority and play considerable role in  
522 antigen uptake by antigen presenting cells (APCs) [30, 31]. In the present study, all prepared  
523 PLGA nanoparticles (rSAG1-PLGA, MPL-PLGA, IMQ-PLGA) shared diameters less than  
524 500 nm which are compatible with desired size mentioned by others. It is worthy to note that  
525 PLGA nanoparticles < 500 nm more potently elicit CTLs (cytotoxic T lymphocytes) response  
526 than larger ones (> 2  $\mu$ m) [32].

527 One of the most critical parameters affecting the size of PLGA-based nanoparticles is  
528 hydrophobicity or water solubility of their cargo [25]. MPL was solved in organic solvents (oil  
529 phase, first emulsion) like PLGA, while IMQ and rSAG1 were solved in aqueous solutions.  
530 Hence, the disruption of MPL into PLGA oil phase resulted in smaller nanoparticles than  
531 those of IMQ and rSAG1. The above-mentioned reason well justifies why the size of MPL-  
532 PLGA was different from the size of IMQ-PLGA and rSAG1-PLGA nanoparticles. All  
533 prepared nanoparticles shared a PDI less than 0.2 indicating more or less homogeneity in the  
534 size of individual nanoparticles. The surface charge similarities among IMQ-PLGA and  
535 MPL-PLGA and blank PLGA nanoparticles were attributed to the method of preparation  
536 (encapsulation) and confirmed that IMQ and PLGA completely have been encapsulated into

537 PLGA nanoparticles, while rSAG1-PLGA showed less negative charge because of rSAG1  
538 adsorption on PLGA nanoparticles [25]. It is worthy to note that we previously proved that  
539 adsorption is a more suitable approach than encapsulation in antigen loading on PLGA  
540 nanoparticles [10]. It should be mentioned that mixing different nanoparticles to prepare two  
541 formulations (PLGA-IMQ + rSAG1-PLGA and PLGA-MPL + rSAG1-PLGA) may affect  
542 nanoparticles features. Thus, the characterizations of different nanoparticles after mixing and  
543 preparing final vaccine formulations are necessary in order to provide better understanding of  
544 nanoparticles behavior at least *in vitro*. Unfortunately, we did not perform these  
545 characterizations before vaccination studies in this research. It should be emphasized that one  
546 of the most critical consequences of stability issues regarding nanoparticles is aggregation  
547 and particle precipitation. As this problem often occurs during time, different PLGA  
548 nanoparticles of each vaccine formulation were mixed just before injection. Fortunately, any  
549 precipitation or aggregation was not observed after mixing different PLGA nanoparticles of  
550 each vaccine formulation. Absolutely, if aggregation was happened, the needle would be  
551 clogged and syringe aspiration and injection to mice would be impossible.

552 Another possible outcome of mixed formulations would be its influence on rSAG1 adsorption  
553 efficiency. In the light of this fact, the mixing of two nanoparticles (rSAG1-PLGA and IMQ-  
554 PLGA or rSAG1-PLGA and MPL-PLGA), and formulations preparation were done exactly  
555 before injection to mice in order to eliminate or decrease any adverse effect of nanoparticles  
556 mixing on rSAG1 adsorption *in-vitro*. Of course, if rSAG1 adsorption was measured after  
557 mixing of different nanoparticles, it could provide satisfying insight in this regard.

558

559 In first experiment, mice vaccinated with the mixture of rSAG1-PLGA and IMQ-PLGA  
560 developed the highest amount of SAG1-specific IgG antibodies, with a mixed Th1/Th2  
561 humoral response biased towards a Th2 response similar to rSAG1-PLGA group (IgG1/IgG2a  
562 OD ratio >2). While, SAG1-specific IgG antibodies titers were higher in mice vaccinated with  
563 the mixture of rSAG1-PLGA and MPL-PLGA in comparison with those vaccinated with the

564 mixture of rSAG1-PLGA and IMQ-PLGA in second experiment, with a more balanced  
565 Th1/Th2-type antibody response (IgG1/IgG2a OD ratio < 2). Therefore, we could deduce that  
566 the formulation rSAG1-PLGA, MPL-PLGA resulted in more potent humoral responses than  
567 rSAG1-PLGA, IMQ-PLGA against SAG1. These findings clearly confirmed the role of IMQ  
568 and MPL in eliciting antibody response against SAG1, although MPL showed higher impact  
569 than IMQ. Mice vaccinated with rSAG1-PLGA and those with the mixture of rSAG1-PLGA  
570 and IMQ-PLGA did not show any significant differences in eliciting IFN- $\gamma$ , IL-2 and TNF- $\alpha$   
571 indicating Th1-biased immunity. Moreover, rSAG1-PLGA + MPL-PLGA group elicited  
572 higher amounts of mentioned cytokines than rSAG1-PLGA + IMQ-PLGA group, though no  
573 significant difference was observed. The less cyst numbers in mice immunized with rSAG1-  
574 PLGA, the mixture of rSAG1-PLGA and IMQ-PLGA, and the mixture of rSAG1-PLGA and  
575 MPL-PLGA were supported by higher amounts of Th1-associated cytokines and anti-SAG1  
576 IgG antibodies in comparison with control groups.

577 The protective efficiency against toxoplasmosis depends on the Th1 immune response [5].  
578 Although antibodies action is limited to extracellular parasites, B-cell antibody responses play  
579 a role in preventing persistent proliferation of tachyzoites in the brain and lung during the  
580 chronic phase of infection [6]. SAG1 contains T epitopes [33, 34] and neutralizing B epitopes  
581 [34-36] and both the cellular responses [34, 38, 39] and the humoral responses [37, 40]  
582 directed against SAG1 were shown to play a role in the protection observed against acute or  
583 chronic *T. gondii* infections. More specifically, in CBA/J or C3H mice (with H-2k haplotype),  
584 parenteral immunizations with SAG1 or SAG1 peptides conferred protection against chronic  
585 *T. gondii* infection following oral challenge with *T. gondii* cysts, when Th1 immune  
586 responses were induced [33, 41]. The brain cyst number in rSAG1-PLGA + MPL-PLGA  
587 group was less than those in rSAG1-PLGA + IMQ-PLGA group. Nevertheless, this difference  
588 was no significant. The lack of any significant difference in cyst number reduction between  
589 rSAG1-PLGA group and rSAG1-PLGA + IMQ-PLGA group is in accordance with their  
590 cytokine profiles and IgG1/IgG2a OD ratio.

591 Immune-enhancing effects of MPL have been reported for a number of antigens, including  
592 *T. gondii* antigens in mouse model [15, 16]. Adjuvant/delivery vehicles containing MPL have  
593 been developed and licensed in FDA-approved vaccines for human use, such as AS04 and  
594 AS01 [42]. Compared to Aluminum salts, AS04 (Aluminium salt + MPL) is more efficient in  
595 inducing the amplification and differentiation of CD4<sup>+</sup> T cells and promotes a Th1-biased  
596 response, MPL therefore provides a counterbalance to the Th2-differentiating properties of  
597 alum [43]. In our experimental conditions, co-administration of rSAG1-PLGA and MPL-

598 PLGA resulted in a more potent humoral response than rSAG1-PLGA and rSAG1-PLGA  
599 plus IMQ-PLGA, with a more polarized Th1 humoral response, confirming the ability of  
600 MPL to promote Th1 bias response. Compared to PLGA, IMQ potentiated the humoral  
601 response but did not potentiate the Th1 humoral response and did not improve the magnitude  
602 of the Th cell response. In present study, the enhanced humoral response obtained by co-  
603 administration of IMQ may be due to B cell–intrinsic TLR7 signaling. This signaling has  
604 been shown to promote vigorous memory B cell responses following co-immunization of an  
605 antigen with IMQ [44]. However, compared to PLGA, IMQ did not potentiate the Th1  
606 humoral response and did not improve the magnitude of the Th cell response. This could be  
607 due to the modest Th1-polarizing responses from TLR7 pDC signaling [45].

608 Our results are similar to those obtained by Kasturi et al. [46] who compared the humoral  
609 responses induced in C57BL/6 mice subcutaneously immunized with hemagglutinin (HA)  
610 from avian influenza H5N1 virus encapsulated in PLGA nanoparticles combined or not with  
611 either PLGA-MPL or PLGA-IMQ nanoparticles. Similar results were also obtained with IMQ  
612 in an anionic liposome formulation, administered by the intramuscular route to C57BL/6  
613 mice with a recombinant *Plasmodium berghei* circumsporozoite protein which was compared  
614 to the TLR4 agonist Glucopyranosyl lipid adjuvant (GLA) [47]. Importantly, compared to  
615 immunization with a single TLR ligand, either IMQ or MPL in PLGA nanoparticles,  
616 immunization with PLGA nanoparticles including both TLR ligands has been shown to  
617 induce synergistic responses. It would be of interest to investigate if whether or not, in our  
618 experimental conditions, combination of PLGA-MPL and PLGA-IMQ could synergize to  
619 enhance the protection. Dendritic cell targeting is also a promising strategy to provide  
620 protection against *T. gondii*. SAG1 targeting to DEC205<sup>+</sup> dendritic cells via an antibody  
621 fragment single-chain fragment variable (scFv) by intranasal and subcutaneous administration  
622 to CBA/J mice has been shown to improve the protection against chronic *T. gondii* infection  
623 [48]. This targeting strategy to dendritic cells, applied to ovalbumin as a model antigen  
624 encapsulated in targeted PLGA nanoparticles together with TLR agonists, led to strong  
625 enhancement of vaccine potency and induction of T cell responses compared to non-specific  
626 delivery of nanoparticles to dendritic cells [49, 50]. Furthermore, as *Toxoplasma* infection is  
627 mainly acquired by consumption of oocysts in contaminated water or vegetables or by  
628 ingestion of tissue cysts contained in infected meat, a vaccine strategy able to induce both  
629 systemic and mucosal immune responses would be of great interest to tackle the parasite at  
630 the portal of entry. Nasal administration is a suitable route to induce such immune responses  
631 and nanoparticles based on PLGA or PLGA derivatives have great potential for this strategy.

632 For example, PLGA nanoparticulate intranasal administration of a combined TLR7/NOD2  
633 agonist with HIV p24 antigen was recently shown to induce high-quality humoral and  
634 adaptive responses both in systemic and mucosal compartments [51]. Since *T. gondii* is an  
635 intracellular parasite with various life cycles and antigenic variations, the development of  
636 effective vaccine against *T. gondii* is a challenging endeavour. This study used SAG1, a well  
637 known candidate vaccine antigen. SAG1 is a major and stage-specific antigen expressed in  
638 *Toxoplasma* tachyzoite and is highly conserved among virulent strains of *T. gondii*.  
639 Combining SAG1 with antigens from the different *T. gondii* stages would undeniably  
640 improve vaccine efficacy.

641 Nowadays, vaccine strategy is implied as a puzzle that all its parts should be accurately  
642 designed and selected in order to achieve immunization goal. These pieces in a vaccine  
643 consist of antigen, adjuvant, delivery system, route of immunization and model.

644

#### 645 **Conclusion**

646 Using SAG1 as a potential candidate vaccine and PLGA nanoparticles as delivery system,  
647 this study indicated that co-delivery of immunomodulators such as TLR agonists and antigens  
648 with PLGA nanoparticles could be appropriate to develop efficacious vaccines against  
649 toxoplasmosis.

650

651

#### 652 **Acknowledgments**

653 Mojgan Allahyari was supported by a PhD research scholar ship from Pasteur Institute of  
654 Iran, Iran (grant N° BD-8831). Also, the recurring funds for this study were supported by  
655 University of Tours. Authors thank B. Héraud for skillful technical assistance.

656

#### 657 **References**

658

659 [1] Tenter AM, Heckeroth AR, Weiss LM. *Toxoplasma gondii*: from animals to humans. IntJ  
660 Parasitol. 2000;30:1217-58. [https://doi.org/10.1016/s0020-7519\(00\)00124-7](https://doi.org/10.1016/s0020-7519(00)00124-7).

661

- 662 [2] Innes EA, Hamilton C, Garcia JL, Chryssafidis A, Smith D. A one health approach to  
663 vaccines against *Toxoplasma gondii*. Food Waterborne Parasitol. 2019 ;15:e00053.  
664 <https://doi.org/10.1016/j.fawpar.2019.e00053>.  
665
- 666 [3] Dunay IR, Gajurel K, Dhakal R, Liesenfeld O, Montoya JG. Treatment of Toxoplasmosis:  
667 Historical Perspective, Animal Models, and Current Clinical Practice. Clin Microbiol  
668 Rev. 2018;31:e00057-17. <https://doi.org/10.1128/CMR.00057-17>.  
669
- 670 [4] Mévélec MN, Lakhrif Z, Dimier-Poisson I. Key Limitations and New Insights Into  
671 the *Toxoplasma gondii* Parasite Stage Switching for Future Vaccine Development in  
672 Human, Livestock, and Cats. Front Cell Infect Microbiol. 2020;10:607198.  
673 <https://doi.org/10.3389/fcimb.2020.607198>.  
674
- 675 [5] Sasai M, Yamamoto M. Innate, adaptive, and cell-autonomous immunity  
676 against *Toxoplasma gondii* infection. Exp Mol Med. 2019;51:1-  
677 [10.https://doi.org/10.1038/s12276-019-0353-9](https://doi.org/10.1038/s12276-019-0353-9).  
678
- 679 [6] Kang H, Remington JS, Suzuki Y. Decreased resistance of B cell-deficient mice to  
680 infection with *Toxoplasma gondii* despite unimpaired expression of IFN-gamma, TNF-  
681 alpha, and inducible nitric oxide synthase. J Immunol. 2000;164:2629-34.  
682 <https://doi.org/10.4049/jimmunol.164.5.2629>.  
683
- 684 [7] Wang Y, Yin H. Research progress on surface antigen 1 (SAG1) of *Toxoplasma gondii*.  
685 Parasit Vectors. 2014;7:180. <https://doi.org/10.1186/1756-3305-7-180>.  
686
- 687 [8] Pagheh AS, Sarvi S, Sharif M, Rezaei F, Ahmadpour E, Dodangeh S, et al. *Toxoplasma*  
688 *gondii* surface antigen 1 (SAG1) as a potential candidate to develop vaccine against  
689 toxoplasmosis: A systematic review. Comp Immunol Microbiol Infect Dis.  
690 2020;69:101414. <https://doi.org/10.1016/j.cimid.2020.101414>.  
691
- 692 [9] Allahyari M, Mohit E. Peptide/protein vaccine delivery system based on PLGA particles.  
693 Hum Vaccin Immunother. 2016;12:806-28.  
694 <https://doi.org/10.1080/21645515.2015.1102804>.  
695

- 696 [10] Allahyari, M., Mohabati, R., Vatanara, A., Golkar, M. In-vitro and in-vivo comparison of  
697 rSAG1-loaded PLGA prepared by encapsulation and adsorption methods as an efficient  
698 vaccine against *Toxoplasma gondii*. J Drug Deliv Sci Technol. 2020;55, 101327.  
699 <https://doi.org/10.1016/j.jddst.2019.101327>.  
700
- 701 [11] Chuang SC, Ko JC, Chen CP, Du JT, Yang CD. Induction of long-lasting protective  
702 immunity against *Toxoplasma gondii* in BALB/c mice by recombinant surface antigen 1  
703 protein encapsulated in poly (lactide-co-glycolide) microparticles. Parasit Vectors.  
704 2013;6:34. <https://doi.org/10.1186/1756-3305-6-34>.  
705
- 706 [12] Roozbehani M, Falak R, Mohammadi M, Hemphill A, Razmjou E, Meamar AR, et al.  
707 Characterization of a multi-epitope peptide with selective MHC-binding capabilities  
708 encapsulated in PLGA nanoparticles as a novel vaccine candidate against *Toxoplasma*  
709 *gondii* infection. Vaccine. 2018;36:6124-6132.  
710 <https://doi.org/10.1016/j.vaccine.2018.08.068>.  
711
- 712 [13] Chuang SC, Ko JC, Chen CP, Du JT, Yang CD. Encapsulation of chimeric protein  
713 rSAG1/2 into poly(lactide-co-glycolide) microparticles induces long-term protective  
714 immunity against *Toxoplasma gondii* in mice. Exp Parasitol. 2013;134:430-7.  
715 <https://doi.org/10.1016/j.exppara.2013.04.002>.  
716
- 717 [14] Dowling JK, Mansell A. Toll-like receptors: the swiss army knife of immunity and  
718 vaccine development. Clin Transl Immunology. 2016;5:e85.  
719 <https://doi.org/10.1038/cti.2016.22>.  
720
- 721 [15] Golkar M, Shokrgozar MA, Rafati S, Musset K, Assmar M, Sadaie R, et al. Evaluation  
722 of protective effect of recombinant dense granule antigens GRA2 and GRA6 formulated  
723 in monophosphoryl lipid A (MPL) adjuvant against *Toxoplasma* chronic infection in  
724 mice. Vaccine. 2007;25:4301-11. <https://doi.org/10.1016/j.vaccine.2007.02.057>.  
725
- 726 [16] Song P, He S, Zhou A, Lv G, Guo J, Zhou J, et al. Vaccination with toxofilin DNA in  
727 combination with an alum-monophosphoryl lipid A mixed adjuvant induces significant  
728 protective immunity against *Toxoplasma gondii*. BMC Infect Dis. 2017;17:19.  
729 <https://doi.org/10.1186/s12879-016-2147-1>.

730  
731  
732  
733  
734  
735  
736  
737  
738  
739  
740  
741  
742  
743  
744  
745  
746  
747  
748  
749  
750  
751  
752  
753  
754  
755  
756  
757  
758  
759  
760  
761  
762

- [17] Stanley MA. Imiquimod and the imidazoquinolones: mechanism of action and therapeutic potential. *Clin Exp Dermatol.* 2002;27:571-7. <https://doi.org/10.1046/j.1365-2230.2002.01151.x>.
- [18] Zaki L, Ghaffarifar F, Sharifi Z, Horton J, Sadraei J. Effect of Imiquimod on Tachyzoites of *Toxoplasma gondii* and Infected Macrophages *in vitro* and in BALB/c Mice. *Front Cell Infect Microbiol.* 2020;10:387. <https://doi.org/10.3389/fcimb.2020.00387>.
- [19] Hamie M, Najm R, Deleuze-Masquefa C, Bonnet PA, Dubremetz JF, El Sabban M, et al. Imiquimod Targets Toxoplasmosis Through Modulating Host Toll-Like Receptor-MyD88 Signaling. *Front Immunol.* 2021;12:629917. <https://doi.org/10.3389/fimmu.2021.629917>.
- [20] Hamdy S, Elamanchili P, Alshamsan A, Molavi O, Satou T, Samuel J. Enhanced antigen-specific primary CD4+ and CD8+ responses by codelivery of ovalbumin and toll-like receptor ligand monophosphoryl lipid A in poly (D,L-lactic-co-glycolic acid) nanoparticles. *J Biomed Mater Res A.* 2007;81:652-62. <https://doi.org/10.1002/jbm.a.31019>.
- [21] Ilyinskii PO, Roy CJ, O'Neil CP, Browning EA, Pittet LA, Altreuter DH, et al. Adjuvant-carrying synthetic vaccine particles augment the immune response to encapsulated antigen and exhibit strong local immune activation without inducing systemic cytokine release. *Vaccine.* 2014;32:2882-95. <https://doi.org/10.1016/j.vaccine.2014.02.027>.
- [22] Kim H, Griffith TS, Panyam J. Poly (d,l-lactide-co-glycolide) Nanoparticles as Delivery Platforms for TLR7/8 Agonist-Based Cancer Vaccine. *J Pharmacol Exp Ther.* 2019;370:715-724. <https://doi.org/10.1124/jpet.118.254953>.
- [23] van de Weert M, Hennink WE, Jiskoot W. Protein instability in poly (lactic-co-glycolic acid) microparticles. *Pharm Res.* 2000;17:1159-67. <https://doi.org/10.1023/a:1026498209874>.



- 763 [24] Allahyari M, Mohabati R, Babaie J, Amiri S, Siavashani ZJ, Zare M, et al. Production of  
764 in-vitro refolded and highly antigenic SAG1 for development of a sensitive and specific  
765 Toxoplasma IgG ELISA. J Immunol Methods. 2015;416:157-66.  
766 <https://doi.org/10.1016/j.jim.2014.11.012>.  
767
- 768 [25] Allahyari M, Mohabati R, Amiri S, Esmaeili Rastaghi AR, Babaie J, Mahdavi M, et al.  
769 Synergistic effect of rSAG1 and rGRA2 antigens formulated in PLGA microspheres in  
770 eliciting immune protection against *Toxoplasma gondii*. Exp Parasitol. 2016;170:236-  
771 246. <https://doi.org/10.1016/j.exppara.2016.09.008>.  
772
- 773 [26] Kazzaz J, Singh M, Ugozzoli M, Chesko J, Soenawan E, O'Hagan DT. Encapsulation of  
774 the immune potentiators MPL and RC529 in PLG microparticles enhances their  
775 potency. J Control Release. 2006;110:566-73.  
776 <https://doi.org/10.1016/j.jconrel.2005.10.010>.  
777
- 778 [27] Ismael AB, Sekkai D, Collin C, Bout D, Mévélec MN. The MIC3 gene of *Toxoplasma*  
779 *gondii* is a novel potent vaccine candidate against toxoplasmosis. Infect Immun.  
780 2003;71:6222-8. <https://doi.org/10.1128/iai.71.11.6222-6228.2003>.  
781
- 782 [28] Couvreur G, Sadak A, Fortier B, Dubremetz JF. Surface antigens of *Toxoplasma gondii*.  
783 Parasitology. 1988 Aug;97 (Pt 1):1-10. doi: 10.1017/s0031182000066695.  
784
- 785 [29] Naeem H, Sana M, Islam S, Khan M, Riaz F, Zafar Z, et al. Induction of Th1 type-  
786 oriented humoral response through intranasal immunization of mice with SAG1-  
787 *Toxoplasma gondii* polymeric nanospheres. Artif Cells Nanomed Biotechnol.  
788 2018;46:1025-1034. <https://doi.org/10.1080/21691401.2018.1478421>.  
789
- 790 [30] Bachmann MF, Jennings GT. Vaccine delivery: a matter of size, geometry, kinetics and  
791 molecular patterns. Nat Rev Immunol. 2010;10:787-96. <https://doi.org/10.1038/nri2868>.  
792
- 793 [31] Danhier F, Ansorena E, Silva JM, Coco R, Le Breton A, Préat V. PLGA-based  
794 nanoparticles: an overview of biomedical applications. J Control Release.  
795 2012;161:505-22. <https://doi.org/10.1016/j.jconrel.2012.01.043>.  
796

- 797 [32] Hamdy S, Haddadi A, Shayeganpour A, Samuel J, Lavasanifar A. Activation of antigen-  
798 specific T cell-responses by mannan-decorated PLGA nanoparticles. *Pharm Res.*  
799 2011;28:2288-301. <https://doi.org/10.1007/s11095-011-0459-9>.  
800
- 801 [33] Velge-Roussel F, Moretto M, Buzoni-Gatel D, Dimier-Poisson I, Ferrer M, Hoebeke J, et  
802 al. Differences in immunological response to a *T. gondii* protein (SAG1) derived  
803 peptide between two strains of mice: effect on protection in *T. gondii* infection. *Mol*  
804 *Immunol.* 1997;34:1045-53. [https://doi.org/10.1016/s0161-5890\(97\)00133-8](https://doi.org/10.1016/s0161-5890(97)00133-8).  
805
- 806 [34] Nielsen HV, Lauemøller SL, Christiansen L, Buus S, Fomsgaard A, Petersen E.  
807 Complete protection against lethal *Toxoplasma gondii* infection in mice immunized  
808 with a plasmid encoding the SAG1 gene. *Infect Immun.* 1999;67:6358-63.  
809
- 810 [35] Mineo JR, McLeod R, Mack D, Smith J, Khan IA, Ely KH, et al. Antibodies to  
811 *Toxoplasma gondii* major surface protein (SAG-1, P30) inhibit infection of host cells  
812 and are produced in murine intestine after peroral infection. *J Immunol.* 1993;150:3951-  
813 64.  
814
- 815 [36] Velge-Roussel F, Dimier-Poisson I, Buzoni-Gatel D, Bout D. Anti-SAG1 peptide  
816 antibodies inhibit the penetration of *Toxoplasma gondii* tachyzoites into enterocyte cell  
817 lines. *Parasitology.* 2001;123:225-33. <https://doi.org/10.1017/s0031182001008460>.  
818
- 819 [37] Fu YF, Feng M, Ohnishi K, Kimura T, Itoh J, Cheng XJ, et al. Generation of a  
820 neutralizing human monoclonal antibody Fab fragment to surface antigen 1 of  
821 *Toxoplasma gondii* tachyzoites. *Infect Immun.* 2011;79:512-7.  
822 <https://doi.org/10.1128/IAI.00969-10>.  
823
- 824 [38] Velge-Roussel F, Marcelo P, Lepage AC, Buzoni-Gatel D, Bout DT. Intranasal  
825 immunization with *Toxoplasma gondii* SAG1 induces protective cells into both NALT  
826 and GALT compartments. *Infect Immun.* 2000;68:969-72.  
827 <https://doi.org/10.1128/iai.68.2.969-972.2000>.  
828

- 829 [39] Mendes EA, Caetano BC, Penido ML, Bruna-Romero O, Gazzinelli RT. MyD88-  
830 dependent protective immunity elicited by adenovirus 5 expressing the surface antigen  
831 1 from *Toxoplasma gondii* is mediated by CD8(+) T lymphocytes. *Vaccine*.  
832 2011;29:4476-84. <https://doi.org/10.1016/j.vaccine.2011.04.044>.  
833
- 834 [40] Siachoque H, Guzman F, Burgos J, Patarroyo ME, Gomez Marin JE. *Toxoplasma gondii*:  
835 immunogenicity and protection by P30 peptides in a murine model. *Exp Parasitol*.  
836 2006;114:62-5. <https://doi.org/10.1016/j.exppara.2006.02.005>.  
837
- 838 [41] Letscher-Bru V, Villard O, Risse B, Zauke M, Klein JP, Kien TT. Protective effect of  
839 vaccination with a combination of recombinant surface antigen 1 and interleukin-12  
840 against toxoplasmosis in mice. *Infect Immun*. 1998;66:4503-6.  
841
- 842 [42] Laupèze B, Hervé C, Di Pasquale A, Tavares Da Silva F. Adjuvant Systems for vaccines:  
843 13 years of post-licensure experience in diverse populations have progressed the way  
844 adjuvanted vaccine safety is investigated and understood. *Vaccine*. 2019;37:5670-5680.  
845 <https://doi.org/10.1016/j.vaccine.2019.07.098>.  
846
- 847 [43] Didierlaurent AM, Morel S, Lockman L, Giannini SL, Bisteau M, Carlsen H, et al.  
848 AS04, an aluminum salt- and TLR4 agonist-based adjuvant system, induces a transient  
849 localized innate immune response leading to enhanced adaptive immunity. *J Immunol*.  
850 2009;183:6186-97. <https://doi.org/10.4049/jimmunol.0901474>.  
851
- 852 [44] Castiblanco DP, Maul RW, Russell Knode LM, Gearhart PJ. Co-Stimulation of BCR and  
853 Toll-Like Receptor 7 Increases Somatic Hypermutation, Memory B Cell Formation, and  
854 Secondary Antibody Response to Protein Antigen. *Front Immunol*. 2017;8:1833.  
855 <https://doi.org/10.3389/fimmu.2017.01833>.  
856
- 857 [45] Dowling DJ. Recent Advances in the Discovery and Delivery of TLR7/8 Agonists as  
858 Vaccine Adjuvants. *Immunohorizons*. 2018;2:185-197.  
859 <https://doi.org/10.4049/immunohorizons.1700063>.  
860

- 861 [46] Kasturi SP, Skountzou I, Albrecht RA, Koutsonanos D, Hua T, Nakaya HI, et al.  
862 Programming the magnitude and persistence of antibody responses with innate  
863 immunity. *Nature*. 2011;470:543-7. <https://doi.org/10.1038/nature09737>.  
864
- 865 [47] Fox CB, Sivananthan SJ, Duthie MS, Vergara J, Guderian JA, Moon E, et al. A  
866 nanoliposome delivery system to synergistically trigger TLR4 AND TLR7. *J*  
867 *Nanobiotechnology*. 2014;12:17. <https://doi.org/10.1186/1477-3155-12-17>.  
868
- 869 [48] Lakhrif Z, Moreau A, Héroult B, Di-Tommaso A, Juste M, Moiré N, et al. Targeted  
870 Delivery of *Toxoplasma gondii* Antigens to Dendritic Cells Promote Immunogenicity  
871 and Protective Efficiency against Toxoplasmosis. *Front Immunol*. 2018;9:317.  
872 <https://doi.org/10.3389/fimmu.2018.00317>.  
873
- 874 [49] Tacke PJ, Zeelenberg IS, Cruz LJ, van Hout-Kuijer MA, van de Glind G, Fokkink RG,  
875 et al. Targeted delivery of TLR ligands to human and mouse dendritic cells strongly  
876 enhances adjuvanticity. *Blood*. 2011;118:6836-44. [https://doi.org/10.1182/blood-2011-](https://doi.org/10.1182/blood-2011-07-367615)  
877 [07-367615](https://doi.org/10.1182/blood-2011-07-367615).  
878
- 879 [50] Cruz LJ, Rosalia RA, Kleinovink JW, Rueda F, Löwik CW, Ossendorp F. Targeting  
880 nanoparticles to CD40, DEC-205 or CD11c molecules on dendritic cells for efficient  
881 CD8(+) T cell response: a comparative study. *J Control Release*. 2014;192:209-18.  
882 <https://doi.org/10.1016/j.jconrel.2014.07.040>.  
883
- 884 [51] Gutjahr A, Papagno L, Vernejoul F, Lioux T, Jospin F, Chanut B, et al. New chimeric  
885 TLR7/NOD2 agonist is a potent adjuvant to induce mucosal immune responses.  
886 *EBioMedicine*. 2020;58:102922. <https://doi.org/10.1016/j.ebiom.2020.102922>.  
887  
888  
889  
890  
891  
892  
893  
894

895 **Table1.** First experiment

896

Groups	Immunization with	Amounts injected to each mouse			Control/Vaccine group	Mice No.	Injection volume
		rSAG1	IMQ	PLGA			
1	rSAG1	20 µg	-	-	Vaccine group	12	100 µl
2	rSAG1-PLGA	20 µg	-	4 mg	Vaccine group	12	100 µl
3	rSAG1-PLGA + IMQ-PLGA	20 µg	64.5 µg	4 mg	Vaccine group	12	100 µl
4	PLGA	-	-	4 mg	Control group	12	100 µl
5	IMQ-PLGA	-	64.5 µg	4 mg	Control group	12	100 µl

897

898

899

900

901

902

903

904

905

906

907

908

909

910

911

912

913

914

915

916

917

918

919

920

921

922

923

924

925

926

927

928

929 **Table 2.** Second experiment

930

Groups	Immunization with	Amounts injected to each mouse				Control/Vaccine group	Mice No.	Injection volume
		rSAG1	IMQ	MPL	PLGA			
1	rSAG1-PLGA + IMQ-PLGA	20 µg	64.5 µg	-	4 mg	Vaccine group	12	100 µl
2	rSAG1-PLGA + MPL-PLGA	20 µg	-	34 µg	4 mg	Vaccine group	12	100 µl
3	IMQ-PLGA	-	64.5 µg	-	4 mg	Control group	4*	100 µl
4	MPL-PLGA	-	-	34 µg	4 mg	Control group	12	100 µl

931

932 \* In this group, 4 mice were injected and were used for the analysis of cellular immune  
 933 response.

934

935

936

937

938

939

940

941

942

943

944

945

946

947

948

949

950

951

952

953

954

955

956

957

958

959

960

961

962


963 **Table 3.** Characterization of IMQ-PLGA, MPL-PLGA, rSAG1-PLGA and blank PLGA  
 964 nanoparticles. Results represent mean  $\pm$  SD of five independent PLGA particle preparation  
 965 batches.  
 966

Formulation	Size (nm)	PDI	Zeta potential (mV)	A/E efficiency (%)	Yield (%)
IMQ-PLGA	451.3 $\pm$ 27	0.15 $\pm$ 0.02	-5.2 $\pm$ 0.26	70 $\pm$ 3.1*	87.3 $\pm$ 2.8
MPL-PLGA	403 $\pm$ 25	0.18 $\pm$ 0.04	-5.6 $\pm$ 0.75	73.1 $\pm$ 1.2*	88.4 $\pm$ 2
rSAG1-PLGA	447 $\pm$ 9	0.11 $\pm$ 0.05	-2.37 $\pm$ 0.3	69.01 $\pm$ 1.8**	88.4 $\pm$ 5.1
Blank PLGA	412 $\pm$ 13	0.10 $\pm$ 0.02	-6.15 $\pm$ 0.7	-	90.3 $\pm$ 2.7

967 PDI; Poly Dispersity Index, A; adsorption, E; encapsulation.

968 \* Encapsulation efficiency, \*\* Adsorption efficiency


969  
 970  
 971  
 972  
 973  
 974  
 975  
 976  
 977  
 978  
 979  
 980  
 981  
 982  
 983  
 984  
 985  
 986  
 987  
 988  
 989  
 990  
 991  
 992  
 993  
 994  
 995

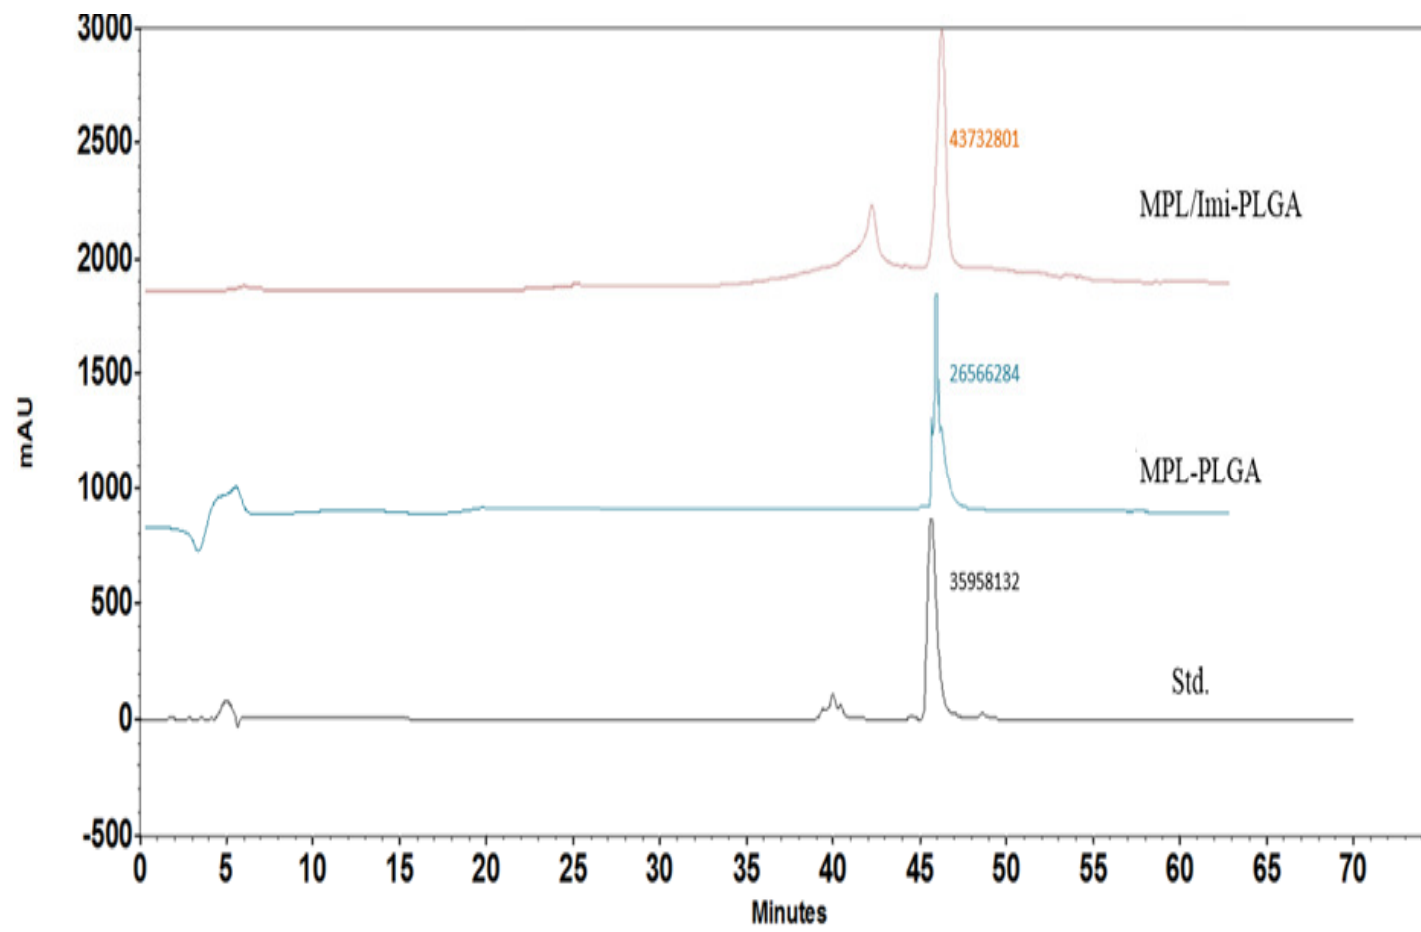




**Figure 2**


**A**

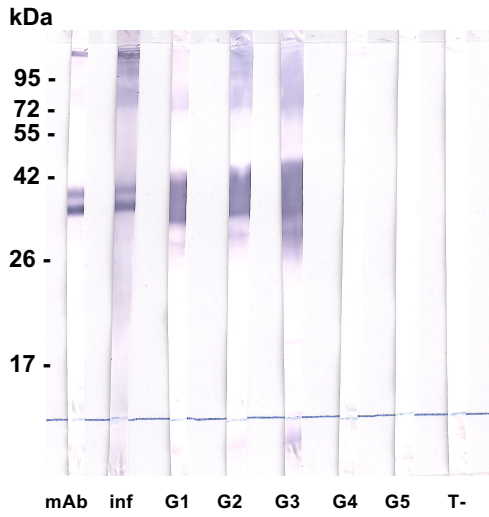


**B**

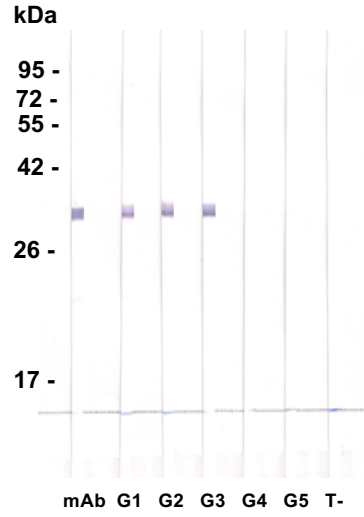


**C**

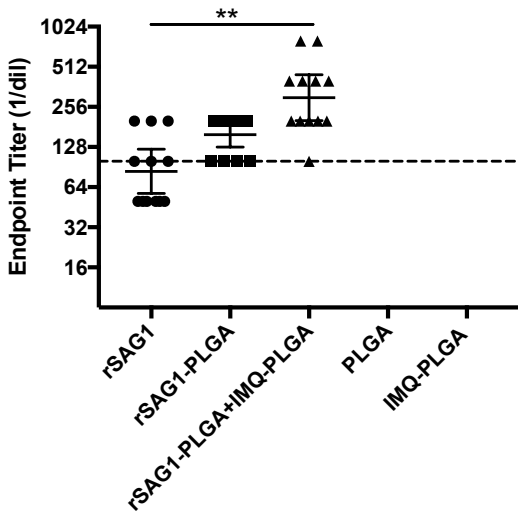

**D**

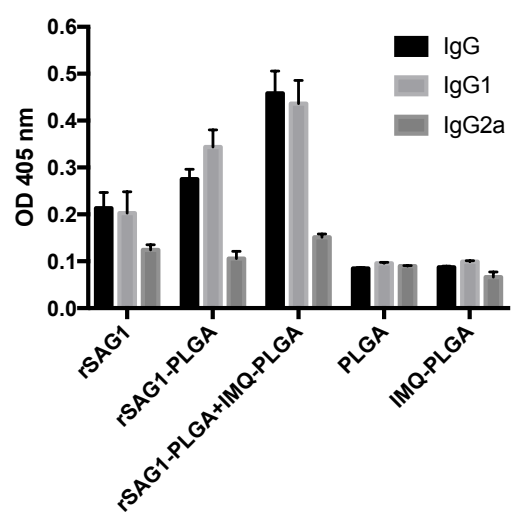

**Figure 3**

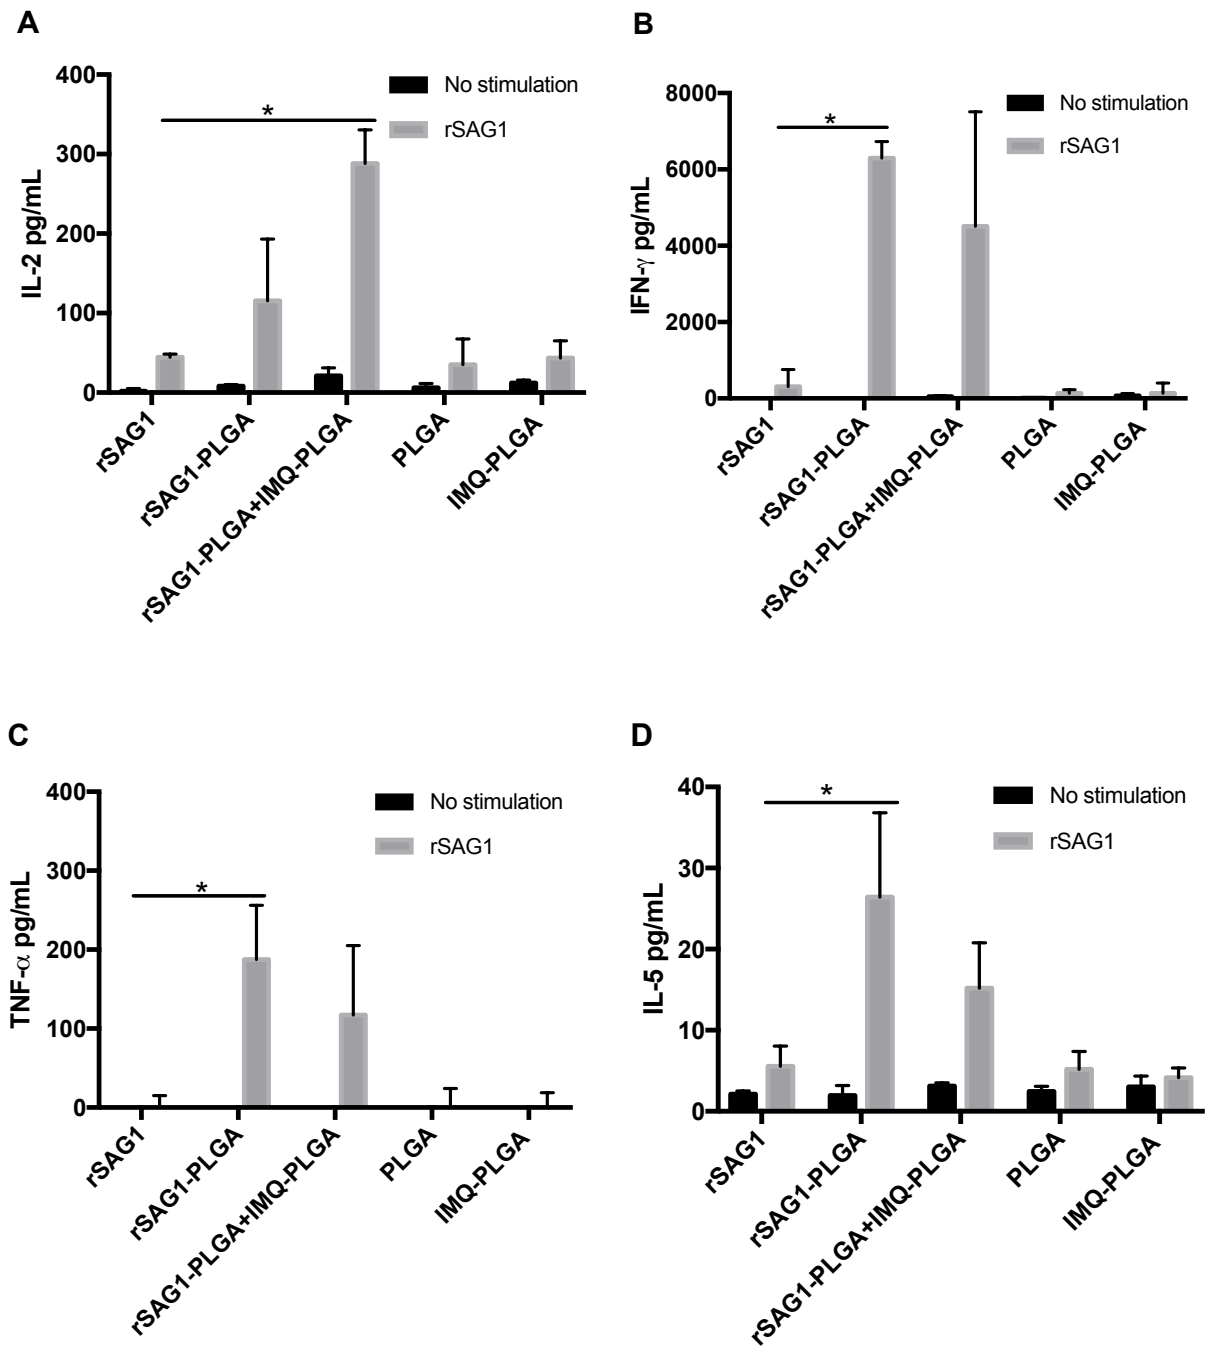

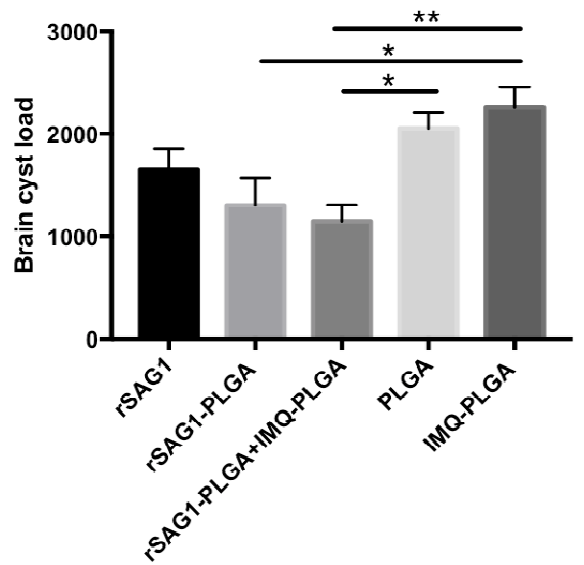


Figure 5

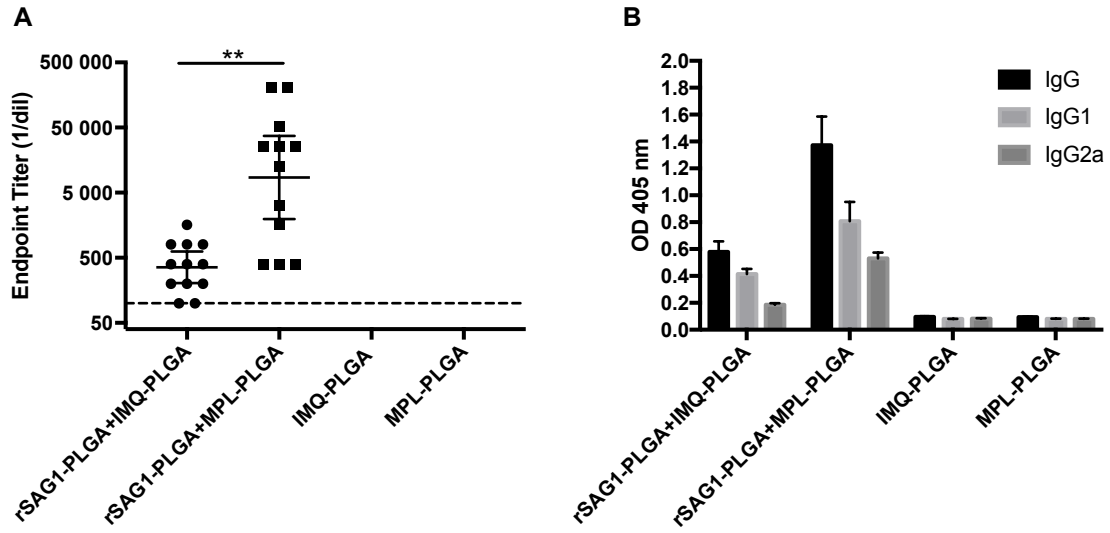


Figure 6

