



HAL
open science

Tio₂ Photocatalytic Biocidal Activity on Escherichia Coli and On Aspergillus Niger under Different Methodological Conditions

Mohamad Al-Hallak, Thomas Verdier, Alexandra Bertron, Christine Roques,
Jean-Denis Bailly

► **To cite this version:**

Mohamad Al-Hallak, Thomas Verdier, Alexandra Bertron, Christine Roques, Jean-Denis Bailly. Tio₂ Photocatalytic Biocidal Activity on Escherichia Coli and On Aspergillus Niger under Different Methodological Conditions. World Congress on Civil, Structural, and Environmental Engineering, CSEE 2023, Mar 2023, Lisbonne, Portugal. 10.11159/icept23.154 . hal-04209650v2

HAL Id: hal-04209650

<https://hal.inrae.fr/hal-04209650v2>

Submitted on 25 Sep 2023

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

TiO₂ Photocatalytic Biocidal Activity on *Escherichia Coli* and On *Aspergillus Niger* under Different Methodological Conditions

Mohamad Al Hallak¹, Thomas Verdier¹, Alexandra Bertron¹, Christine Roques², Jean-Denis Bailly³

¹Laboratoire Matériaux et Durabilité des Constructions (LMDC), INSA Toulouse,
135 avenue de Rangueil, 31400 Toulouse, France

²Laboratoire Génie Chimique (LGC), Université de Toulouse, CNRS, INPT, UPS
35 chemin des Maraîchers, 31400 Toulouse, France

³Laboratoire de Chimie Agro-industrielle (LCA), Université de Toulouse, INRA, INPT
4 allées Emile Monso, 12 31030, Toulouse, France

alhallak@insa-toulouse.fr; tverdier@insa-toulouse.fr; bertron@insa-toulouse.fr; roques730@aol.com; jean-denis.bailly@envt.fr;

Abstract – Biological pollution is one major cause of the degradation of indoor air quality. It was shown that microbial communities from outdoor might impact significantly the communities detected indoor. In addition, microbial contamination of the surfaces of building materials and their release into the indoor air also significantly affect indoor air quality. Preventing the growth or at least reducing the amounts of microorganisms growing on indoor building materials is essential for reducing health risks for building occupants. Photoactive TiO₂ has been widely studied as a photocatalyst that enable the inactivation of various bacterial strains. In this paper, we compare the antifungal activity of nanoparticles of TiO₂ on *Aspergillus niger* spores and its antibacterial activity on *Escherichia coli* under low light irradiation, near to common indoor values. The antimicrobial activity of TiO₂, expressed as log reduction, was assessed under UV irradiation in a sludge mixture of sterile water, suspension and nanoparticles of TiO₂. The results showed a strong bactericidal activity of TiO₂ on *E. coli* and a weak fungicidal activity against *A. niger*. Different parameters including concentration of TiO₂, intensity of light, and duration of contact between TiO₂ and microbial cells and spores, were investigated and significantly affected the antibacterial activity of TiO₂ while poorly affected its antifungal activity. Results of this study confirmed previous investigations on antibacterial activity of TiO₂ on *E. coli* and bring new insight on antifungal activity on the spores of *A. niger*. The effectiveness of the antimicrobial activity is enhanced by the duration of contact between suspension and TiO₂ nanoparticles through the stirring experiments for 2H, 4H and 24H.

Keywords: Bactericidal activity, Fungicidal activity, Indoor air, Aerosolization, Photocatalysis, TiO₂

1. Introduction

Indoor air pollution is an important cause of serious health problems for occupants including respiratory diseases, allergic symptoms, cancers and cardiovascular problems[1–9]. For several years now, there is an increased awareness to the effect of indoor air quality on human health and wellbeing[1,10]. Actually, people spend 80%-90% of their times indoors[11,12] so it's important to understand the main causes of indoor air pollution and find suitable solutions to ameliorate indoor air quality. The world health organization (WHO) reported in 2009 that biological pollution is one major cause for the degradation of indoor quality[13,14]. Indoor investigations have highlighted that microbial contamination of surfaces of building materials may have a significant impact on the microbial communities present indoors. However, quantitative evaluation of such impact is only little studied. When promoting conditions (humidity and nutrient content) are available, building materials are exposed to microbial growth[1,15]. Upon their growth on surfaces, microorganisms produce aerial particles such as spores, toxins, volatile organic compounds and other metabolites that can be inhaled by occupants[16–20]. To prevent or to reduce microbial contamination on surfaces, the antimicrobial activity of several chemical products has already been studied. They include semi-conductors products such as titanium dioxide (TiO₂), zinc oxide (ZnO), gallium arsenide, tungsten (VI) oxide (WO₃), gallium phosphide, and cadmium but also alternative products such as fatty acid and glycerol esters[21–23]. Titanium dioxide (TiO₂) is widely recognized as one of the most efficient photocatalysts used for air purification[21,22]. It has excellent optical and electronic properties, high photocatalytic activity, high chemical stability, non-toxicity, low cost, availability, and abundance[22]. Under “high” intensities of light, over >10 W/m², the photocatalysis of TiO₂ nanoparticles showed strong antimicrobial activity against a wide variety of microorganisms, including algae, viruses, bacteria and fungi [24–27]. Nevertheless, few studies have been carried out in the last five years investigating the effect of TiO₂ on various microorganisms at lower levels of intensity (≤5W/m²), closed to real-world conditions (30W/m² in sunny days and 5-10W/m² in cloudy days outdoors and 4-5 W/m² indoors)[21,28–30].

The objective of this study was to investigate the efficiency of TiO₂ nanoparticles on *Escherichia coli* and *Aspergillus niger* through direct contact between microbial suspension and photocatalyst TiO₂ under different experimental conditions

(concentration of TiO₂ nanoparticles, light intensity and duration of contact). Experiments were carried in dark, and under light real-life irradiation using 8W black-light bulbs at 5W/m².

2. Materials And Methods

2.1 Microbial cultivation and preparation of suspensions

Most frequently detected microorganisms in the indoor environment (on surfaces of building materials and airborne) are (i) Gram negative bacteria and mycobacteria[15,31], (ii) fungal genera such as *Aspergillus*, *Penicillium*, *Cladosporium* and *Stachybotrys*[31–34]. In this study, *Escherichia coli* and *Aspergillus niger* were chosen to evaluate TiO₂ nanoparticles antimicrobial activity.

E. coli CIP 53126 was obtained from the collection of the Pasteur Institute (CIP), Paris, France. Strains were stored at –80 °C in his Eugon medium (Biomérieux, Craaponne, France) supplemented with 10% glycerol. Bacterial cells were pre-cultured on trypticase soy agar (TSA) before each experiment (incubation 36 °C ± 1 °C for 16-24 h). A new subculture was performed (36 °C ± 1 °C for 16-20 hours) prior to testing. For testing, bacterial cells were dispersed in 1/500 broth (NB)[21,31,35] and the bacterial cell content of the inoculum suspension was determined using a spectrophotometer (640 nm) at approximately 10⁸ cells/mL. The cell suspension was then diluted 10-fold and 1 mL of each dilution was plated incorporated in TSA to determine the number of CFU/mL.

For fungal suspension, *A. niger* strain CBS 733.88 was cultured in a flask, on Sabouraud agar medium (SAB) (Biomérieux) at 22.5 °C for 10 to 14 days to prepare the spore suspension[36]. Ten mL of sterilized distilled water + tween 80 with sterile glass balls were inserted into the flask of strain and the flask was shaken gently for at least 2 minutes. The suspension was then collected and filtered through sterile frit 080557-2 (40-100 µm) into a sterile pot containing sterile glass beads to prevent clustering of spores. The concentration of suspension was obtained by counting spores on Malassez cell through optical microscope. One mL of suspension adjusted to 1*10⁷ cfu/mL was inoculated into SAB Petri dishes and then incubated at 22°C for 48 h before CFU counts.

2.2 Stirring experiment: Evaluation of antimicrobial activity of TiO₂

During each experiment, 1mL was taken from each beaker at t₀=0 min and every 30 minutes for 2 or 4 hours and ten-fold diluted in sterile distilled water for CFU numerations (as for the suspensions). Petri dishes from *E. coli* experiments and *A. niger* experiments were incubated at 36°C ±1°C for 48 hours and at 30°C ±1°C for 48 hours respectively. The antimicrobial activity (log reduction) was then calculated using Equation 1.

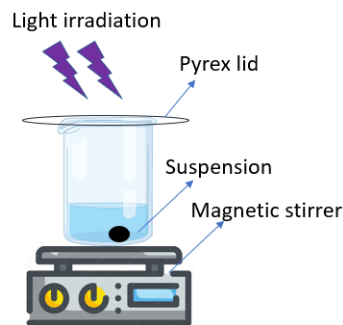


Figure 1: A schema illustrating the stirring experiment: Magnetic stirrer at 300 rpm; Beaker containing suspension: (*E. coli* or *A. niger*), TiO₂ in test tubes or distilled water in control tubes; Light irradiation of 5 W/m² in light conditions; Pyrex lid.

$$R = \text{Log}(C_{\text{susp}}) - \text{Log}(C_{\text{test}}) = \text{Log}\left(\frac{C_{\text{susp}}}{C_{\text{test}}}\right) \quad \text{Equation 1}$$

Where R: Log₁₀ Reduction of TiO₂ (referred as antimicrobial activity in the text), C_{susp}: Average concentration of suspension in control tube without TiO₂, C_{test}: Average concentration of suspension in test tube with TiO₂ in CFU/mL.

Each experiment was repeated at least twice and results present the average obtained from each series of experiments with corresponding standard deviations (SD).

3. Results And Discussion

3.1 Effect of TiO₂ in the dark

In the dark, after two hours of contact between 10g/L TiO₂ and cell/spore suspension, the average log₁₀ reduction was 0.04±0.01 for *A. niger* suspension and 2.27±0.08 for *E. coli* (Figure 2). These results are in agreement with previous findings regarding TiO₂ efficacy[37]. The strong antibacterial activity may be explained by the ability of well-dispersed nano-particles of TiO₂ to interact with bacterial cells absorbing them to their surfaces and leading to a remarkable decrease in their concentration[38]. Regarding antifungal activity, the resistance of fungal spores to TiO₂[37,39] implies no interaction between nanoparticles of TiO₂ and fungal spores of *A. niger* and thus a negligible fungicidal activity was observed after 2 hours of contact in the dark.

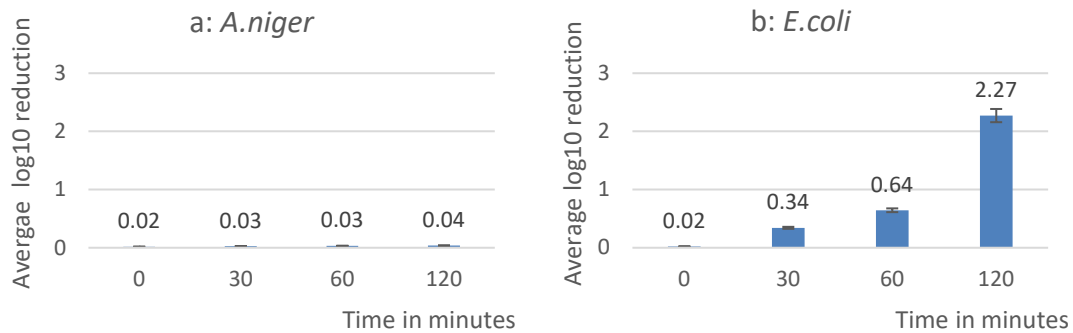


Figure 2: Average ±SD of log reduction of 10g/L TiO₂ in dark conditions on *A. niger* suspension (a) vs on *E. coli* (b).

3.2 Effect of TiO₂ under light

Under a light intensity of 5W/m², both antifungal and antibacterial activity of 10g/L TiO₂ were evaluated. After 2 hours of contact between suspension and TiO₂, the average log₁₀ reduction ‘R’ was 0.85±0.03 for *A. niger* spore suspension and 2.58±0.08 for *E. coli*. TiO₂ shows a weaker activity on *A. niger* spores compared to its activity on *E. coli* cells (Figure 3). Previous findings showed a higher antifungal activity of TiO₂ mixed with Ag nanoparticles on *Aspergillus niger* but these results were obtained using a very high light intensity of 40W/m²[40] or by continuous UV irradiation for 20 days[39]. The ability of TiO₂ to damage the cell membrane of *E. coli* explains its high antibacterial activity[22,41]. The differences between fungal cell membranes and bacterial ones may also contribute to the difference of TiO₂ effects observed in our study[42,43].

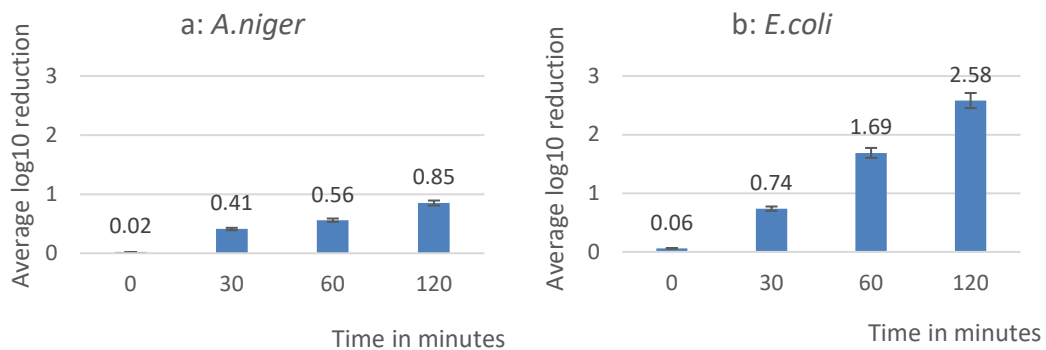


Figure 3: Average ± SD of log reduction of 10g/L TiO₂ in light conditions on *A. niger* suspension (a) vs on *E. coli* (b).

3.3 Influence of the concentration of TiO₂ on its antibacterial activity

The antibacterial activity of TiO₂ was tested at 10g/L where it showed $R > 2.00$ in dark and light conditions. Another series of experiments was carried at 1g/L concentration of TiO₂ to investigate its activity on *E. coli* at a lower concentration tested previously by Verdier[21]. In the dark, after 4 hours of contact, 1g/L of TiO₂ showed a clearly weaker activity compared to that observed after 2 hours of contact to 10g/L TiO₂ with only 0.61 ± 0.01 log reduction (Figure 4). By contrast, under light, 4 hours of contact to 1g/L TiO₂ showed approximately similar antibacterial activity as that of 10g/L TiO₂ after 2 hours of contact. The maximum log reduction was 2.49 ± 0.07 after 4 hours of contact for 1g/L and 2.58 ± 0.08 after 2 hours of contact for 10g/L of TiO₂ (Figure 5). As said before, high concentration of TiO₂ (10g/L) was capable to inhibit the growth and/or kill the cells of *E. coli* either by damaging their cell membranes under light[22,41], or by absorbing them onto their surfaces in the dark[38]. At low concentration (1g/L), the number of well dispersed nano-particles of TiO₂ might not be sufficient to interact directly with bacterial cells and reduce their concentrations in the dark, whereas under the light, the antibacterial activity of 1g/L of TiO₂ may be explained by its capability to damage cell membrane of *E.coli* when photocatalyzed (Figure 4). The reduced concentration of TiO₂ requires therefore a longer application time to be active. As an illustration, concentrations of TiO₂ as low as 0.1g/L have shown a strong antibacterial activity but after 24 hours of contact using a light intensity range of 14- 55 W/m²[44].

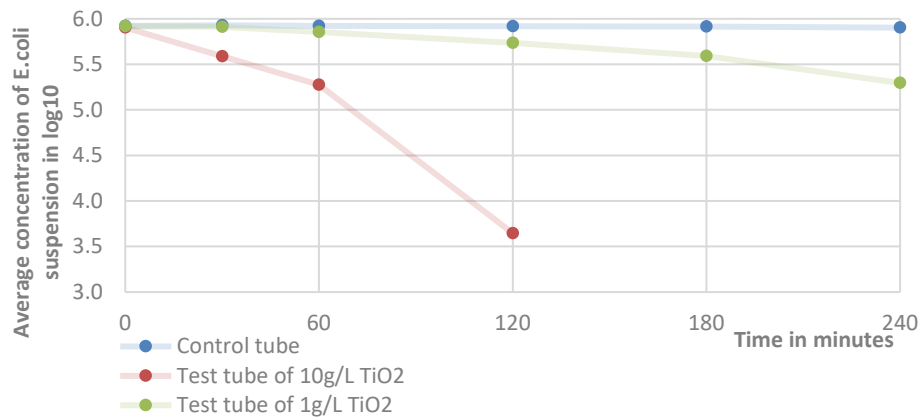


Figure 4: Variation with time of average concentration of *E. coli* suspension (log CFU) in the dark in: control tube; test tube containing 10g/L of TiO₂; test tube containing 1g/L of TiO₂.

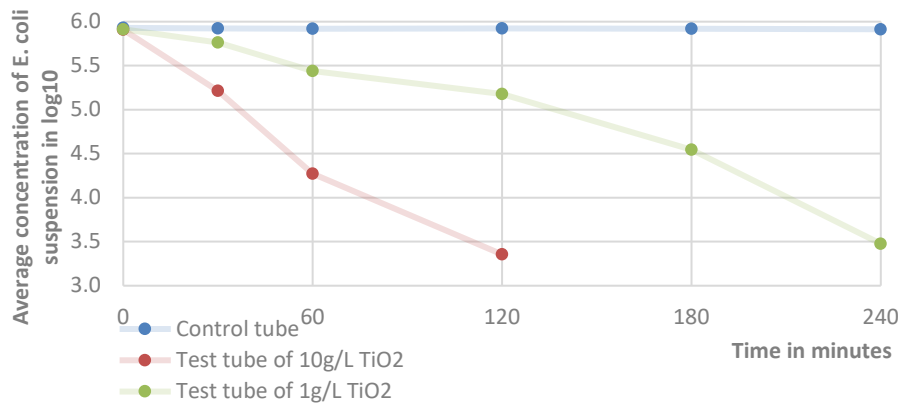


Figure 5: Variation with time of average concentration of *E. coli* cell suspension (log CFU) under light conditions in: control tube; test tube containing 10g/L of TiO₂; test tube containing 1g/L of TiO₂.

3.4 Resistance of *Aspergillus niger* to TiO₂ photocatalyst

To investigate the resistance of *A. niger*, another series of stirring experiments was carried out for 24 hours of contact between *A. niger* and TiO₂ in light conditions. After 24 hours of contact, the resistance of *A. niger* against the photocatalyst TiO₂ was confirmed as the maximum reduction reached was only 0.86±0.02 (Figure 6). No study has previously highlighted the resistance of *A. niger* to the photocatalyst TiO₂ within real-life conditions. One investigation has shown the ability of TiO₂ to inhibit the growth of *A. niger* on woods but these results were obtained at very high light intensities[39]. By contrast, our results are in agreement with the resistance of *A. niger* against TiO₂ observed after 24 hours of contact in the dark[37].

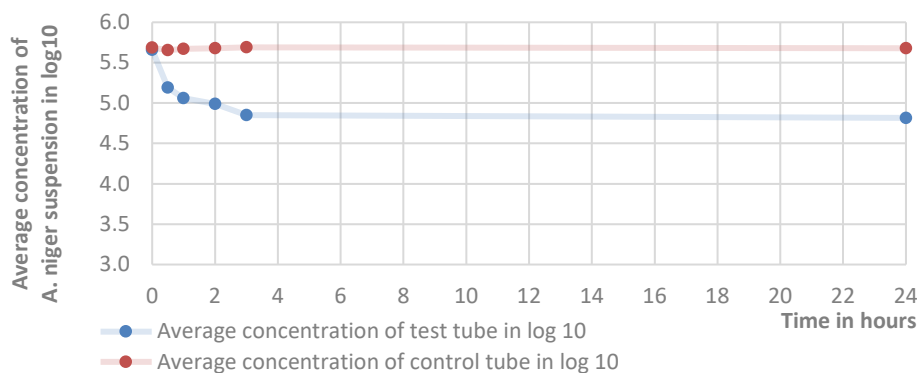


Figure 6: Variation with time of average concentration of *A. niger* spore suspension (log CFU) in control tube and in test tube during contact with TiO₂ nanoparticles for 24 hours in light conditions

4. Conclusion

The main objective of this study was to investigate the difference between the antibacterial effect from one side and antifungal effect on other side of TiO₂ nanoparticles through stirring experiments allowing a direct contact between TiO₂ and cells at low light intensity close to real-world conditions. The obtained results confirmed previous findings on the antibacterial activity of TiO₂ on *E. coli* and highlighted the variation of its efficiency as a function of its concentration, duration of contact, light/dark conditions and especially as a function of microorganisms (Spores of *A. niger* vs *E. coli* in current study). TiO₂ is an efficient photocatalyst, non-toxic and a low-cost product that is employed in most air and water purification systems using high light intensities[22]. In addition, this substance is already used in coatings, paints, and in cementitious materials[31,45]. Indeed, as the antibacterial activity of TiO₂ nanoparticles is important, it is also essential to highlight the resistance of other microorganisms such as some fungal spores to this product. The inclusion of particles such as fungal spores may affect negatively the efficiency of TiO₂ on vegetative cells suggesting that the application of TiO₂ nanoparticles in paint[21] is perhaps not the best way to use it. These findings suggest the limitation of photocatalytic products interest in the destruction of microorganisms under common indoor light irradiation. On the basis of new research, their applications should be aimed toward prevention through growth inhibition.

Acknowledgements

The authors would like to thank Université Paul Sabatier Toulouse III and the Région Occitanie (Project SoBio2QAI) for their financial support.

References

1. AL HALLAK, M. Fungal Contamination of Building Materials, Aerosolization of Particles and Toxins in the Indoor Air and Associated Risk for Health: A Review. *Manuscript submitted for publication* 2023.
2. Saini, J.; Dutta, M.; Marques, G. A Comprehensive Review on Indoor Air Quality Monitoring Systems for Enhanced Public Health. *Sustainable Environment Research* **2020**, *30*, 6, doi:10.1186/s42834-020-0047-y.

3. Viegi, G.; Simoni, M.; Scognamiglio, A.; Baldacci, S.; Pistelli, F.; Carrozzi, L.; Annesi-Maesano, I. Indoor Air Pollution and Airway Disease [State of the Art]. *The International Journal of Tuberculosis and Lung Disease* **2004**, *8*, 1401–1415.
4. Tran, V.V.; Park, D.; Lee, Y.-C. Indoor Air Pollution, Related Human Diseases, and Recent Trends in the Control and Improvement of Indoor Air Quality. *International Journal of Environmental Research and Public Health* **2020**, *17*, 2927, doi:10.3390/ijerph17082927.
5. Vural, S.M. Indoor Air Quality. In *Sick Building Syndrome: in Public Buildings and Workplaces*; Abdul-Wahab, S.A., Ed.; Springer: Berlin, Heidelberg, 2011; pp. 59–74 ISBN 978-3-642-17919-8.
6. Turiel, I. *Indoor Air Quality and Human Health*; Routledge, 1998; ISBN 978-0-419-13870-9.
7. Norhidayah, A.; Chia-Kuang, L.; Azhar, M.K.; Nurulwahida, S. Indoor Air Quality and Sick Building Syndrome in Three Selected Buildings. *Procedia Engineering* **2013**, *53*, 93–98, doi:10.1016/j.proeng.2013.02.014.
8. Agarwal, N.; Meena, C.S.; Raj, B.P.; Saini, L.; Kumar, A.; Gopalakrishnan, N.; Kumar, A.; Balam, N.B.; Alam, T.; Kapoor, N.R.; *et al.* Indoor Air Quality Improvement in COVID-19 Pandemic: Review. *Sustainable Cities and Society* **2021**, *70*, 102942, doi:10.1016/j.scs.2021.102942.
9. Baudet, A.; Baurès, E.; Guegan, H.; Blanchard, O.; Guillaso, M.; Le Cann, P.; Gangneux, J.-P.; Florentin, A. Indoor Air Quality in Healthcare and Care Facilities: Chemical Pollutants and Microbiological Contaminants. *Atmosphere* **2021**, *12*, 1337, doi:10.3390/atmos12101337.
10. World Health Organization. Regional Office for Europe *WHO Guidelines for Indoor Air Quality: Selected Pollutants*; World Health Organization. Regional Office for Europe, 2010; ISBN 978-92-890-0213-4.
11. Lai, H.K.; Kendall, M.; Ferrier, H.; Lindup, I.; Alm, S.; Hänninen, O.; Jantunen, M.; Mathys, P.; Colville, R.; Ashmore, M.R.; *et al.* Personal Exposures and Microenvironment Concentrations of PM_{2.5}, VOC, NO₂ and CO in Oxford, UK. *Atmospheric Environment* **2004**, *38*, 6399–6410, doi:10.1016/j.atmosenv.2004.07.013.
12. Vardoulakis, S.; Kinney, P. Grand Challenges in Sustainable Cities and Health. *Frontiers in Sustainable Cities* **2019**, *1*.
13. Alberti, C.; Bouakline, A.; Ribaud, P.; Lacroix, C.; Rousselot, P.; Leblanc, T.; Derouin, F. Relationship between Environmental Fungal Contamination and the Incidence of Invasive Aspergillosis in Haematology Patients. *Journal of Hospital Infection* **2001**, *48*, 198–206, doi:10.1053/jhin.2001.0998.
14. Ayanbimpe, G.M.; Danjuma, W.S.; Okolo, M.O. *Relationship between Fungal Contamination of Indoor Air and Health Problems of Some Residents in Jos*; IntechOpen London, England, 2012; Vol. 2012;.
15. Verdier, T.; Coutand, M.; Bertron, A.; Roques, C. A Review of Indoor Microbial Growth across Building Materials and Sampling and Analysis Methods. *Building and Environment* **2014**, *80*, 136–149, doi:10.1016/j.buildenv.2014.05.030.
16. PATRICK, J.M. A Review of: “Indoor Air Pollutants: Exposure and Health Effects; Euro Reports and Studies 78” (1983). *Ergonomics* **1985**, *28*, 1504–1505, doi:10.1080/00140138508963278.
17. Shariat, C.; Collard, H.R. Acute Lung Injury after Exposure to *Stachybotrys Chartarum*. *Respiratory Medicine Extra* **2007**, *3*, 74–75, doi:10.1016/j.rmedx.2007.03.001.
18. Li, X.; Liu, D.; Yao, J. Aerosolization of Fungal Spores in Indoor Environments. *Science of The Total Environment* **2022**, *820*, 153003, doi:10.1016/j.scitotenv.2022.153003.
19. Aleksic, B.; Draghi, M.; Ritoux, S.; Bailly, S.; Lacroix, M.; Oswald, I.P.; Bailly, J.-D.; Robine, E. Aerosolization of Mycotoxins after Growth of Toxinogenic Fungi on Wallpaper. *Applied and Environmental Microbiology* **83**, e01001-17, doi:10.1128/AEM.01001-17.
20. Kim, K.-H.; Kabir, E.; Jahan, S.A. Airborne Bioaerosols and Their Impact on Human Health. *Journal of Environmental Sciences* **2018**, *67*, 23–35, doi:10.1016/j.jes.2017.08.027.
21. Verdier, T.; Coutand, M.; Bertron, A.; Roques, C. Antibacterial Activity of TiO₂ Photocatalyst Alone or in Coatings on *E. Coli*: The Influence of Methodological Aspects. *Coatings* **2014**, *4*, 670–686, doi:10.3390/coatings4030670.
22. Dharma, H.N.C.; Jaafar, J.; Widiastuti, N.; Matsuyama, H.; Rajabsadeh, S.; Othman, M.H.D.; Rahman, M.A.; Jafri, N.N.M.; Suhaimin, N.S.; Nasir, A.M.; *et al.* A Review of Titanium Dioxide (TiO₂)-Based Photocatalyst for Oilfield-Produced Water Treatment. *Membranes (Basel)* **2022**, *12*, 345, doi:10.3390/membranes12030345.

23. Verdier, T.; Bertron, A.; Valentin, R.; Boussambe, G.N.M.; Mouloungui, Z.; Roques, C. Monoglyceride to Protect Building Materials against Microbial Proliferation. *Matériaux & Techniques* **2016**, *104*, 508, doi:10.1051/mattech/2017018.
24. Dalrymple, O.K.; Stefanakos, E.; Trotz, M.A.; Goswami, D.Y. A Review of the Mechanisms and Modeling of Photocatalytic Disinfection. *Applied Catalysis B: Environmental* **2010**, *98*, 27–38, doi:10.1016/j.apcatb.2010.05.001.
25. Ateia, M.; Alalm, M.G.; Awfa, D.; Johnson, M.S.; Yoshimura, C. Modeling the Degradation and Disinfection of Water Pollutants by Photocatalysts and Composites: A Critical Review. *Science of The Total Environment* **2020**, *698*, 134197, doi:10.1016/j.scitotenv.2019.134197.
26. Benabbou, A.K.; Derriche, Z.; Felix, C.; Lejeune, P.; Guillard, C. Photocatalytic Inactivation of Escherichia Coli: Effect of Concentration of TiO₂ and Microorganism, Nature, and Intensity of UV Irradiation. *Applied Catalysis B: Environmental* **2007**, *76*, 257–263, doi:10.1016/j.apcatb.2007.05.026.
27. Foster, H.A.; Ditta, I.B.; Varghese, S.; Steele, A. Photocatalytic Disinfection Using Titanium Dioxide: Spectrum and Mechanism of Antimicrobial Activity. *Appl Microbiol Biotechnol* **2011**, *90*, 1847–1868, doi:10.1007/s00253-011-3213-7.
28. Lux, K.C. Synthesis and gold decoration of alternative oxides to TiO₂ for the photocatalytic degradation of NO and NO₂ in indoor environment conditions: Evaluation of the efficiency and the contribution of the decoration on the photocatalytic activity. phdthesis, INSA de Toulouse, 2022.
29. Menazea, A.A.; Awwad, N.S. Antibacterial Activity of TiO₂ Doped ZnO Composite Synthesized via Laser Ablation Route for Antimicrobial Application. *Journal of Materials Research and Technology* **2020**, *9*, 9434–9441, doi:10.1016/j.jmrt.2020.05.103.
30. Falco, G.D.; Porta, A.; M. Petrone, A.; Gaudio, P.D.; Hassanin, A.E.; Commodo, M.; Minutolo, P.; Squillace, A.; D’Anna, A. Antimicrobial Activity of Flame-Synthesized Nano-TiO₂ Coatings. *Environmental Science: Nano* **2017**, *4*, 1095–1107, doi:10.1039/C7EN00030H.
31. Verdier, T.; Bertron, A.; Erable, B.; Roques, C. Bacterial Biofilm Characterization and Microscopic Evaluation of the Antibacterial Properties of a Photocatalytic Coating Protecting Building Material. *Coatings* **2018**, *8*, 93, doi:10.3390/coatings8030093.
32. Borrego, S.; Molina, A. Fungal Assessment on Storerooms Indoor Environment in the National Museum of Fine Arts, Cuba. *Air Qual Atmos Health* **2019**, *12*, 1373–1385, doi:10.1007/s11869-019-00765-x.
33. Górný, R.L.; Reponen, T.; Willeke, K.; Schmechel, D.; Robine, E.; Boissier, M.; Grinshpun, S.A. Fungal Fragments as Indoor Air Biocontaminants. *Applied and Environmental Microbiology* **2002**, doi:10.1128/AEM.68.7.3522-3531.2002.
34. Hegarty, B.; Haverinen-Shaughnessy, U.; Shaughnessy, R.J.; Peccia, J. Spatial Gradients of Fungal Abundance and Ecology throughout a Damp Building. *Environ. Sci. Technol. Lett.* **2019**, *6*, 329–333, doi:10.1021/acs.estlett.9b00214.
35. An Overview of Methods Used to Evaluate the Efficacy of Antibacterial Treated Surfaces and Textiles 2012.
36. Ph., Eur. *European Pharmacopoeia*; 2022; Vol. 11;.
37. Yu, K.-P.; Huang, Y.-T.; Yang, S.-C. The Antifungal Efficacy of Nano-Metals Supported TiO₂ and Ozone on the Resistant Aspergillus Niger Spore. *Journal of Hazardous Materials* **2013**, *261*, 155–162, doi:10.1016/j.jhazmat.2013.07.029.
38. Sohm, B.; Immel, F.; Bauda, P.; Pagnout, C. Insight into the Primary Mode of Action of TiO₂ Nanoparticles on Escherichia Coli in the Dark. *PROTEOMICS* **2015**, *15*, 98–113, doi:10.1002/pmic.201400101.
39. Chen, F.; Yang, X.; Wu, Q. Antifungal Capability of TiO₂ Coated Film on Moist Wood. *Building and Environment* **2009**, *44*, 1088–1093, doi:10.1016/j.buildenv.2008.07.018.
40. Rahmat, N.; Wahyuni, E.T.; Suratman, A. Antifungal Activity of TiO₂/Ag Nanoparticles under Visible Light Irradiation. *Indonesian Journal of Chemistry* **2020**, *21*, 14–23, doi:10.22146/ijc.49150.
41. Liu, P.; Duan, W.; Wang, Q.; Li, X. The Damage of Outer Membrane of Escherichia Coli in the Presence of TiO₂ Combined with UV Light. *Colloids and Surfaces B: Biointerfaces* **2010**, *78*, 171–176, doi:10.1016/j.colsurfb.2010.02.024.

42. Gao, X.; Swarge, B.N.; Dekker, H.L.; Roseboom, W.; Brul, S.; Kramer, G. The Membrane Proteome of Spores and Vegetative Cells of the Food-Borne Pathogen *Bacillus Cereus*. *International Journal of Molecular Sciences* **2021**, *22*, 12475, doi:10.3390/ijms222212475.
43. Qiu, S.; Ma, F.; Wo, Y.; Xu, S. Study on the Biological Effect of Tourmaline on the Cell Membrane of *E. Coli*. *Surface and Interface Analysis* **2011**, *43*, 1069–1073, doi:10.1002/sia.3694.
44. Ibáñez, J.A.; Litter, M.I.; Pizarro, R.A. Photocatalytic Bactericidal Effect of TiO₂ on *Enterobacter Cloacae*: Comparative Study with Other Gram (–) Bacteria. *Journal of Photochemistry and Photobiology A: Chemistry* **2003**, *157*, 81–85, doi:10.1016/S1010-6030(03)00074-1.
45. Maury-Ramirez, A.; De Muynck, W.; Stevens, R.; Demeestere, K.; De Belie, N. Titanium Dioxide Based Strategies to Prevent Algal Fouling on Cementitious Materials. *Cement and Concrete Composites* **2013**, *36*, 93–100, doi:10.1016/j.cemconcomp.2012.08.030.